

1 How much cement can we do without? Lessons from
2 cement material flows in the UK

3 W. Shanks^a, C. F. Dunant^{a,*}, Michał P. Drewniok^a, R. C. Lupton^a, A. Serrenho^a, Julian
4 M. Allwood^a

5 ^a*Department of Engineering, University of Cambridge, Trumpington Street, Cambridge CB2 1PZ, UK*

6 **Abstract**

Cement manufacture is responsible for 5-7 % of world CO₂ emissions. Cement is primarily used in concrete, the most used material on the planet and a critical part of any analysis of emissions reduction strategy. To estimate the potential for reducing demand, this work analyses material flow in the cement industry, using the UK in 2014 as a case study. Combining published data, analytic assumptions, and interviews we estimated the material flow of cement from the production to a breakdown of its use in applications. Having broken down the demand for cement into 25 applications, multiple material efficiency techniques were considered: substituting cement for calcined clay and limestone, reducing the cement content of concrete, post-tensioning floor slabs, using more precast building elements, reducing construction waste, and reducing the overdesign in construction. We produce a final estimate of the total reduction in emissions achievable from material efficiency: 51.3 %. Due to overlap and interactions between the methods, the attribution of the carbon abatement depends on the sequence of application. In this analysis, we have applied the reduction of overdesign last, because it is independent of the others, and would require a cultural change. We show then that cement demand from floors, repairs and maintenance, concrete beams, and applications within the transport sector should be targeted. The substitution of cement with calcined clay and limestone has the biggest potential to reduce cement demand (27 %) and carbon emissions in the UK. Reducing the amount of cement in concrete has the next highest

*Corresponding author

potential (10 %), followed by post-tensioning floor slabs (3 %).

7 *Keywords:* Material efficiency, Material Flows, Cement, Carbon emissions

8 **1. Introduction**

9 Cement is the most consumed material in the world (Low, 2005). We make more
10 than four billion tonnes of it every year — 560 kg for every person alive (van Oss,
11 2017). It is one of society's most ubiquitous, cheap and useful materials. Mixed with
12 water and sand it makes mortar, or more commonly it is used as a binder in concrete
13 which. Producing clinker, the primary ingredient in cement, requires heating limestone
14 to 1450° C. Burning fossil fuels is the predominant method used to provide energy for
15 the process, accounting for 40-50 % of emissions; additionally, limestone decomposes
16 upon heating, accounting for the remaining 50-60 % (Van den Heede and De Belie,
17 2012). These emissions account for 5-7 % of global CO₂ emissions (Mathieu, 2006);
18 in the UK this value is about 1 % (UK Government - Department for Business, Energy
19 and Industrial Strategy, 2016). Cement demand is projected to increase (International
20 Energy Agency, 2018), so its manufacture is key in any global decarbonisation pathway.
21 Efforts to reduce the energy-related emissions include reducing the dependence on fossil
22 fuels and research into carbon capture and storage for cement plants. Further strategies
23 involves reducing the process emissions of cement by reducing demand for clinker
24 using fly ash (FA) and ground granulated blast-furnace slag (GGBFS) or capturing the CO₂
25 released.

26 *Process and energy related emissions.* Much of the progress in decarbonisation has been
27 made in energy-related emissions and the potential for further efficiency improvements
28 appears to be limited. Clinker is produced in cement kilns whose energy intensity
29 can vary widely. However, globally. only 14 % of clinker is still produced outside
30 of dry kilns, in wet kilns which have to supply additional energy to evaporate water.
31 There is therefore limited scope for further improvement (World Business Council for

32 Sustainable Development - Cement Sustainability Initiative, 2016). Waste heat can
33 be captured from cement kilns and used to generate ‘green’ electricity, to the order
34 of about 30 % of input heat (World Business Council for Sustainable Development -
35 Cement Sustainability Initiative, 2016; Schneider et al., 2011). This estimation appears
36 optimistic, however, and in the UK, no significant opportunities to exploit kiln waste
37 heat have been identified (Department for Business, Energy & Industrial Strategy and
38 Mineral Products Association, 2017). Electricity demand accounts for up to 10 % of
39 the CO₂ emissions associated with cement production (Van den Heede and De Belie,
40 2012). This has been mitigated to some extent with on-site renewables and demand-side
41 flexibility. However, any possible further improvement here is minimal: a case study
42 of an optimised electricity schedule was found to reduce electricity-derived emissions
43 by only 4 % (Summerbell et al., 2017). Providing heat with biomass or waste instead
44 of fossil fuels is a further method to reduce greenhouse gas emissions associated with
45 cement production. While this switch has been partially achieved in the UK, Griffin et al.
46 (2014) argues that availability of waste fuels and competition for biomass may be a
47 limiting factor.

48 More than half of the carbon emissions released by cement manufacture are ‘process’
49 emissions from the thermal decomposition of limestone. Carbon capture and storage
50 (ccs) is one way of mitigating these emissions, whereby CO₂ is captured and stored
51 underground after it has been produced (Li et al., 2013). The International Energy
52 Agency predicts that ccs could reduce global emissions from cement production by 56 %
53 on today’s value (International Energy Agency and The World Business Council for Sus-
54 tainable Development, 2009). ccs is currently an immature technology, particularly with
55 respect to cement manufacture: there has so far been no industrial-scale demonstration
56 of the technology on a cement plant anywhere in the world. In the UK, only one kiln has
57 a large enough throughput to be considered economically viable for ccs retrofit (Griffin
58 et al., 2014). Pathways to decarbonisation cannot confidently rely on ccs technology.

59 *Material and supply-side options.* Clinker substitution is a successful and established
60 mitigation strategy. Fly ash (FA), a by-product of coal-fired power plants, and ground
61 granulated blast furnace slag (GGBFS), a by-product of the steel industry, are both suitable
62 for this purpose (Leese and Casey, 2015). These materials do not alter the process
63 emissions from producing clinker, but have significantly lower embodied emissions than
64 clinker, and in reducing the need for it they lower the embodied emissions of the final
65 material used. Currently, they account for about 20 % of cementitious material used
66 in the UK cement and concrete industries. This has significantly reduced the emissions
67 intensity of UK cement: Portland cement (Portland cement) embodies 0.930 kg of
68 CO₂ for every kg made, while the average embodied emissions associated with UK
69 cementitious material is 0.787 kg — a 15 % reduction (Leese and Casey, 2015). There
70 are however limitations on the availability of these materials, both in the UK and globally
71 (Damineli and John, 2012). The International Energy Agency and The World Business
72 Council for Sustainable Development (2009) estimate that globally clinker substitution
73 with these materials can only account for a reduction in emissions of 10 % on today's
74 value.

75 Griffin finds that in the UK, under a 'radical transition scenario', emissions will
76 only be reduced by 50 % on 2010 levels by 2050 whereas the entire economy needs to
77 decarbonise by about 70 % to adhere to the 2008 Climate Change Act (Griffin et al.,
78 2014; Government of the United Kingdom, 2008). The decarbonisation of the cement
79 sector cannot be achieved without improving material efficiency (Allwood et al., 2011)
80 and reducing demand. There are numerous studies that consider individual methods of
81 reducing cement demand from a specific application — using ultra-high performance
82 concrete (Wille and Boisvert-Cotulio, 2015) or post-tensioning of concrete floor slabs
83 (Abdelrahman, 2017) — but there are no wider analyses of which efficiency techniques
84 have the greatest potential, or which the easiest to implement might be.

85 Some work has attempted to evaluate how cement is used. For example McEvoy

86 et al. (2004) have applied a ‘mass balance approach’ to construction material flow
87 in the North West of England estimating construction materials’ destinations by end-
88 sector. Similarly, a breakdown of construction materials in Ireland into their end-sector
89 proportions is given by Woodward and Duffy (2011) . Their study describes the mass
90 flows of ready-mix concrete, concrete blocks and other prefabricated parts. The authors
91 also consider the end of life and the waste management stage of the industry. However,
92 their work does not detail finely the final applications of cement. Wang et al. (2016)
93 analyses flows in the Chinese cement industry. Their study gives numerical relationships
94 between inputs and outputs in relevant processes. However, in their analysis, cement
95 products are only broken down into mortar and concrete. There are multiple instances of
96 material flow analyses of specific elements of the cement life cycle. For example, Gao
97 et al. (2016) aim to quantify mass flows in the clinker production process. Broadhead
98 (2017) performs a material flow analysis on the global life-cycle of cement but with
99 limited resolution in end-use applications and does not quantify material efficiency
100 benefits.

101 To aid planning and life cycle analysis, Kapur et al. (2008) modelled stocks of
102 cement in the United States. Their study achieved higher resolution of cement’s end-
103 use than those previously mentioned: it broke the uses of cement down in to ‘end-use
104 markets’ such as water and waste management, commercial buildings etc. Unfortunately,
105 this resolution is insufficient to assess material efficiency improvements, which depend
106 on applications. Similarly Cao et al. (2017b) propose a wide historical and prospective
107 view of the use of cement at the scale of countries. Cao et al. (2017a) modelled of
108 the stocks of cement in end-sectors in China. However, no estimation of the stocks
109 within individual applications was reported. Also studying China, Fernández (2007)
110 broke material consumption in urban areas down into different types of construction.
111 Unfortunately, the results were not specific enough in terms of applications to aid this
112 study.

113 Currently, there is no holistic understanding of the techniques that could improve
114 cement use, nor do we have the knowledge to assess which of these techniques could
115 have the biggest effect. This work aims to fill this gap, by:

- 116 • understanding where cement is used and the processes involved in going from
117 raw materials to detailed applications
- 118 • quantifying, by application, the extent to which demand can be reduced through
119 various ‘material efficiency’ techniques
- 120 • verifying the results of this analysis with the construction industry.

121 Using the results of this analysis, recommendations can be made as to which applications
122 should be targeted and which material efficiency measures could have the biggest impact.
123 These recommendations should be realistic and implementable; uncertainty in the
124 analysis is assessed where possible and the limitations of the proposals are discussed.

125 **2. Methods**

126 This section details the methods used to map the flow of material in the cement
127 industry in the UK. Subsequently, material efficiency measures and their effects on
128 demand and carbon emissions are assessed on an application-specific basis. An estimate
129 of the total possible reduction in cement demand and resultant emissions savings is also
130 derived.

131 *2.1. Mapping material flow*

132 Material flow analysis (MFA as per Brunner and Rechberger (2003)) was used to build
133 a map of the flow of materials in the cement industry, from raw materials to end-use
134 applications. Published data were used to map from extraction to cement production.
135 The uncertainties associated with these data were estimated so that more reliable data
136 could be identified and contradictory sources compared. Case studies, relationships and

137 estimation were used to estimate the breakdown of demand for cement from its final
138 applications.

139 *Defining the system boundary.* System boundaries must be specified to avoid incorrect
140 inclusion or exclusion of data. The UK's cement industry was chosen as the area to be
141 studied: data are much more widely available there than globally. The time frame studied
142 was 2014 as this was the most recent year with data widely available. Occasionally,
143 data for other years had to be used, either under the assumption that the value does not
144 change significantly year on year, or by scaling up from bottom-up samples.

145 *Defining the system structure.* Limestone or dolomite or chalk (or a mixture) and clay
146 or shale are mined. In 'raw meal processing', they are crushed and milled into fine
147 particles, then dried. This raw meal is fed into a kiln and heated to 1450 °C by burning
148 fuel. In the kiln, several chemical reactions occur, releasing CO₂, kiln dust and the
149 desired product, clinker, which is a mixture of calcium aluminates and calcium silicates.
150 Clinker is cooled and ground into a fine powder with 0-5 % gypsum. The resulting grey
151 powder is Portland cement. Small amounts of FA, GGBFS or limestone fines can also be
152 added at this blending stage. This process is the so-called 'dry bed process' which is to
153 our knowledge the only one used in the UK.

154 Portland cement can then be mixed further with the additions FA and GGBFS to alter
155 its properties and reduce the final product's embodied carbon. This can be done either
156 at the cement plant, or during concrete production. In the EU there are 27 different types
157 of cement, based on their proportions of clinker, gypsum, FA, GGBFS, limestone and other
158 materials. Each type falls into one of five classes (CEM I-V¹ as per EN BS 197-1).

159 Cement is then mixed with fine aggregates (sand), coarse aggregates (gravel) and
160 water to make concrete, or without coarse aggregates to make a paste called mortar.
161 Concrete production can occur in three main ways: ready-mix, where the wet mixture is
162 poured '*in-situ*'; precast, where concrete products are made in a factory then assembled

¹CEM I is the same as Portland cement.

163 on-site; or retail, where cement is bought in bags and mixed at a small scale (this ranges
 164 from small do-it-yourself project to small amounts of mortar mixed by contractors).
 165 While it makes up only 10-15 % of concrete's mass, cement accounts for 80+ % of
 166 its carbon emissions (in the case of CEM I) (Dewar, 2003; Teh et al., 2017). This
 167 investigation is motivated by carbon emissions and so cement and its ingredients were
 168 the materials tracked in the MFA. Water and aggregates, concrete's other constituents
 169 that account for far less of the overall emissions, were not. Figure 1 illustrates the path
 170 from raw materials to structure, and indicates where the material efficiency techniques
 171 proposed in this paper would apply.

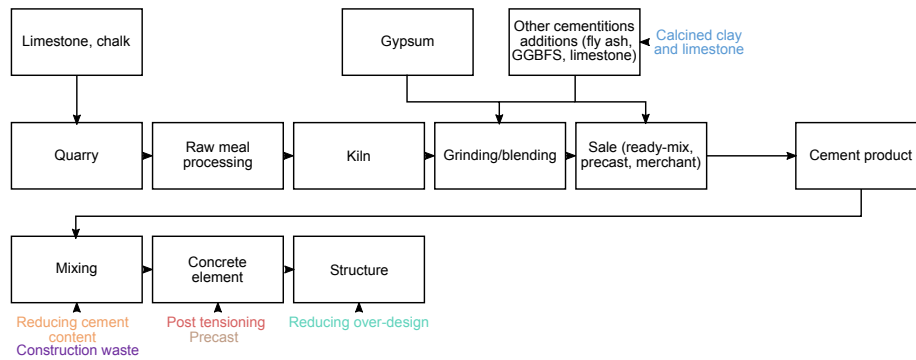


Figure 1: Flow diagram illustrating the cement industry processes and materials studied in this MFA. We have also added the points at which the material efficiency techniques would intervene.

172 *Key assumptions.* Data sources rarely specify which cement class is used, let alone give
 173 a breakdown of cementitious materials used. Some concrete products are typically made
 174 with a specific class of cement. For instance, concrete in very large foundations will
 175 use GGBFS to reduce the heat of hydration and prevent cracking (Sun et al., 2013; Tang
 176 et al., 2015). This kind of information is not available for most applications. In Part II
 177 of the MFA, all cement and cementitious materials were aggregated into one material,
 178 therein labelled 'cement' and it was assumed that this single material was used in all
 179 applications.

180 Additionally, the amount of cement in concrete varies from product to product

181 (usually 200-300 kg/m³) and is not always specified. The cement content depends on
182 location, temperature, availability of other materials (such as high quality aggregates)
183 and can also vary due to human interference on site or designers' choices. Therefore,
184 data on concrete production and concrete use in specific applications do not necessarily
185 translate directly to cement use in that application. Where it was necessary to work
186 backwards from concrete data to cement use, an average cement content had to be
187 assumed.

188 *Performing the MFA — Part I: From raw materials to cement.* The first part of the
189 MFA required mapping material flows from extraction through various processes to the
190 production of cement, and the forms in which it is sold: precast, ready-mix or small-scale
191 'retail' cement. This was done by collecting and harmonising published data to form a
192 coherent map. Uncertainty here was estimated, and any missing data accounted for.

193 Data are reported on raw material extraction, material throughput of kilns, clinker
194 production and broadly the use of additions. Nearly all cementitious material flow in
195 the UK is covered by these data, which were collated in a database. Their sources are
196 summarised in Table 1. The sum of all raw materials, plus additions, less the waste
197 from the production of clinker comes to 13,030 kt. The Mineral Products Association
198 estimates that total cementitious material used in the cement industry in Great Britain in
199 2014 comes to 12,433 kt. When scaled by population (Great Britain comprises ~97 %
200 of the population of the UK), this translates to material use of 13,040 kt in the UK — a
201 strong level of agreement.

202 For this part of the MFA, the uncertainty associated with each data point was estimated.
203 There are multiple possible sources of uncertainty in material flow analysis, described
204 below.

205 **Unavailable data** There are no available data for certain flows, either because they are
206 not recorded, or because they are not released for competitive reasons.

207 **Data reporting** Data can be reported in a number of different forms: production quan-

Table 1: The sources of data used in Part I of the MFA.

| Material references | <i>Notes</i> |
|--|--|
| Clay/shale UK Government (2016); British Geological Survey (2014) | <i>Used to make raw meal</i> |
| Limestone/ dolomite/ chalk UK Government (2016); British Geological Survey (2014) | <i>Used to make raw meal</i> |
| Clinker UK Government Department for Business and Strategy (2017) | <i>Total produced from raw meal and used to make cement</i> |
| Waste — | <i>Waste by-products from the kiln</i> |
| Gypsum World Business Council for Sustainable Development - Cement Sustainability Initiative (2016) | <i>Added with clinker to the blending process</i> |
| Ground limestone & fines World Business Council for Sustainable Development - Cement Sustainability Initiative (2016) British Precast - Mineral Products Association (2015) | <i>Added with clinker to the blending process</i> |
| Exported cement Mineral Products Association (2015a) | <i>Cement produced in the UK and sold abroad</i> |
| Imported cement Mineral Products Association (2015a) | <i>Cement produced abroad and sold in the UK</i> |
| Portland cement British Precast - Mineral Products Association (2015) | <i>UK Portland cement production</i> |
| Fly ash UK Quality Ash Association (2016) British Precast - Mineral Products Association (2015) World Business Council for Sustainable Development - Cement Sustainability Initiative (2016) | <i>Added: with clinker to the blending process; to retail cement; to ready-mix concrete; to precast concrete</i> |
| Blast furnace slag UK Government - Competition Commission (2016) European Ready Mixed Concrete Organization (2017) British Precast - Mineral Products Association (2015) | <i>Added: to ready-mix concrete; with clinker to the blending process</i> |
| Quicklime British Precast - Mineral Products Association (2015) | <i>Quicklime added to precast concrete</i> |
| Ready-mix Mineral Products Association (2015a) | <i>Cementitious material that is used in ready mix concrete</i> |
| Precast Mineral Products Association (2015a) | <i>Cementitious material that is used in precast concrete</i> |
| Retail cement Mineral Products Association (2015a) | <i>Cementitious material that is used in retail applications</i> |
| Other cement Mineral Products Association (2015a) | <i>Cementitious material that is used in other applications</i> |

208 tities, sales, deliveries or stocks. For a consistent MFA, the differences between
209 of each of these should be considered. Because cement has a relatively short
210 shelf-life, stocks are generally sparse and data are usually reported as sales.

211 **Anachronous or foreign data** The best available data may fall outside the system
212 boundary. This data can be included in the MFA, but appropriate consideration of
213 the uncertainty that this produces is necessary. Some data were reported for Great
214 Britain (Scotland, Wales and England). The subject of this study was the United
215 Kingdom (Great Britain + Northern Ireland) so to account for this disparity, when
216 no data could be found for Northern Ireland, values were scaled with population.
217 This adds about 3 % onto the mass flow. Due to the relatively small change, errors
218 introduced here should be small.

219 **Clarity of data** It is not always clear what the data are referring to, especially in an
220 industry like cement's which can be complex due to the number of different
221 materials involved.

222 **Estimating the uncertainty** the uncertainty of each data point was characterised by
223 using the method of Laner et al. (2015) to systematically quantify coefficients of
224 variation (CVs). Assuming uncertainties are described by normal distributions,
225 the CV is the ratio between the standard deviation s_i and mean X_i of each data
226 point i (Equation 1), with the true value expected to fall within $2s_i$ of the mean
227 95 % of the time.

$$\text{Coefficient of variation } CV_i = s_i/X_i \quad (1)$$

228 The coefficient of variation for each data point was determined by scoring each
229 data source from 1 (very good) to 4 (questionable quality) on its *reliability*,
230 *completeness*, *temporal correlation*, *geographical correlation*, and *other corre-*
231 *lation* (e.g. similarity of material categories). To yield a quantified uncertainty

232

characterisation these scores were mapped into CVs according to Equation 2:

$$CV = \begin{cases} ae^{b \cdot \text{score}} & \text{for the } \textit{reliability} \text{ category} \\ ae^{b \cdot (\text{score}-1)} & \text{for other categories with score} > 1 \\ 0 & \text{for other categories with score} = 1 \end{cases} \quad (2)$$

233

with default settings of the parameters of $a = 0.375$ and $b = 1.105$ (Laner et al.,

234

2015). Finally, to give a single CV representing all sources of uncertainty for the

235

data source, the individual CVs were combined according to Equation 3:

$$CV_{\text{total}} = \sqrt{\sum_{c \in \text{all categories}} CV_c^2} \quad (3)$$

236

Manipulation of data and ‘reconciliation’ was performed when multiple sources

237

report on the same flow. If these sources are judged to be in general agreement

238

relative to their size, an average flow, f , can be found which is also characterised

239

as a normal distribution with mean X_f and standard deviation s_f . This is done

240

according to Equations 4.

$$X_f = \sqrt{\frac{\sum_i^n \frac{X_i}{s_i^2}}{\sum_i^n \frac{1}{s_i^2}}} \quad ; \quad s_f = \sqrt{\frac{1}{\sum_i^n \frac{1}{s_i^2}}} \quad (4)$$

241

This method was used for the masses of FA and GGBFS being added in the production

242

of Portland cement, FA added in the production of Portland cement, GGBFS added

243

to ready-mix concrete and FA added to precast concrete.

244

Occasionally the mass flows reported by data sources disagree sufficiently that the

245

average could not be a reliable representation of the true value. There are several

246

possible reasons why they do not agree: they are erroneously labelling the same flow

247

but are in reality referring to different ones (*e.g.* one is referring to total cement while

248

the other to only CEM I), one is an estimate while the other is based on measurement, or

249

one is simply incorrect. In these cases, the uncertainty estimates were used to decide

250 which the more reliable source was, with the others being ignored. This was necessary
251 for the masses of limestone/dolomite/chalk and clay/shale used to make raw meal.

252 *Performing the MFA — Part II: From cement to applications.* No data are published on
253 the demand for cement for any application. The methods used in this part of the MFA were
254 an attempt to estimate this information, and are described below grouped by end-use
255 sector. An application is an individual product that cement is used in (*e.g.* mortar for
256 bricks, dense concrete blocks, foundations etc.) The relevant features of an application
257 are: end-use sector (residential buildings, non-residential buildings, infrastructure,
258 repairs and maintenance, other), building type (if applicable), building frame type (if
259 applicable), and the material it is made from (concrete, non-concrete, unspecified). The
260 applications included in the MFA were generally dictated by the availability of data;
261 applications for which there was no way of estimating cement use were grouped into an
262 ‘other’ category.

263 Data on concrete demand from each *end-use sector* was provided by CEMBUREAU
264 (2017). This source supplied data for the UK for 2007-2009, so errors will have been
265 introduced when assuming that they apply to 2014, due to the inevitable changes in
266 demand over time. To check that these data are accurate, they were compared to the
267 financial outlay in 2014 of the relevant construction sectors published by the Office for
268 National Statistics (2015). These data align extremely well, due to economic conditions
269 in 2014 being at the level of 2008 see *e.g.* Office for National Statistics (2018b,c). The
270 CEMBUREAU data were therefore considered a sound basis from which to underpin other
271 calculations, under the assumption that industry spending and concrete demand are
272 correlated. Following this, the breakdowns of cement use within each sector were
273 calculated.

274 **Concrete in steel- and concrete-framed buildings** A breakdown of the uses of ce-
275 ment within buildings is needed. The relative use of concrete in *beams, columns*
276 *and floor slabs* in a *concrete framed building* was given by a case study from

277 the Singapore Building and Construction Authority (2012), and confirmed as
278 being accurate by industry experts. Concrete ground floors were approximated as
279 150mm, while a regular (first floor or above) slab is approximately 280 mm (Neal,
280 2002; Eyre, 2006).

281 To calculate the cement demand from columns, we calculated the mass of slabs
282 required, assuming a load of 5.5 kN/m² after Coelho et al. (2004), for buildings
283 up to 10 floors. A spreadsheet was made which calculated, for buildings of height
284 from 1-10 floors, the mass of the floor slabs. From this and the case study above,
285 demand for cement in columns and beams can be estimated. Cement demand in
286 *foundations* for concrete-framed buildings can then be estimated as a function of
287 the weight and live load of the building (assumed to be 5 kN/m² (Formichi, 2008)),
288 using a representative soil load-bearing capacity of 150 kPa, and assuming point
289 load transfer from columns to foundations. The foundations can be approximated
290 as cubes just large enough so that the pressure imparted on the soil will not cause
291 it to collapse. Larger buildings will use piles and/or rafts, but these only represent
292 a small fraction of all construction. The foundation size for a particular building
293 therefore depends on the floor area and number of storeys. The results given by
294 the spreadsheet were not very sensitive to slab self-weight, and were minimally
295 sensitive to the assumed live-load.

296 This breakdown varies with number of stories; an average breakdown was cal-
297 culated using the building heights distribution shown in Figure 2. To test the
298 sensitivity of this breakdown to the building height distribution, it was shifted
299 ‘upwards’ — 3 storeys were added on to every building such that the mean floor
300 height was 6.13. The shares between floors, foundations, columns and beams in
301 the final breakdown changed by <1 % each (the relative shares between ground
302 floors and floor slabs did change more significantly, however similar material
303 efficiency techniques can be applied to these applications so this uncertainty is

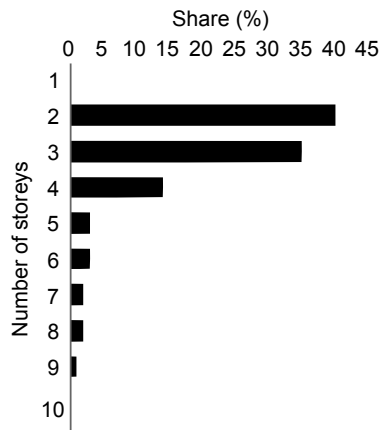


Figure 2: The distribution of building storey-number for steel- and concrete-framed buildings used in this analysis, adapted from the UK Government (2010) (p. 11). This source reported the share of flats of storey height 1-5, 6+, and is assumed to apply to all non-residential buildings as well because no data on heights of offices etc. are reported. The mean number of storeys in this distribution is 3.13.

304 not critical).

305 It is difficult to estimate how much concrete is used in *cores*. It was assumed that
 306 cores are only used in concrete frames above around 15 floors. This would mean
 307 that few buildings have a core; a total demand of 3 % within a concrete frame was
 308 used as an estimate. The breakdown was verified during interviews with design
 309 engineers, and found to be in agreement with their numbers. Further, for a seven
 310 storey concrete-framed building, the output of this method aligns extremely well
 311 with a case study by López-Mesa et al. (2009).

312 The relative proportions of concrete use between floors, foundations and cores
 313 for *steel-framed buildings* was done in the same fashion as for concrete-framed
 314 buildings. For every building height of 1-10 storeys, the mass of foundations
 315 was calculated based on the mass of concrete floor slabs and live-load capacity
 316 required, assuming that the mass of steel elements would be minimal compared
 317 to these slabs. It was difficult to calculate the amount of concrete used for cores;
 318 they are generally used for steel buildings above about 8 storeys and a 6 % share
 319 was used as an approximation.

320 **Concrete blocks** The annual production areas (m² of face) of the three main types of
 321 *concrete block* — lightweight, dense and autoclaved aerated (AAC) — are published
 322 by the UK Government Department for Business and Strategy (2017). Assuming
 323 an average block volume of 440 × 215 × 100 mm (CBA, 2008), the number of
 324 each type of block can be calculated. A survey of concrete blocks provided their
 325 average masses: 20 kg, 25 kg and 14 kg respectively. The cement content by
 326 mass of the three types of block was kindly provided by John Mason of Thomas
 327 Armstrong Ltd. as “somewhere between 7-12 % by weight typically. For instance,
 328 a dense block requires less cement than a lightweight block due to the stronger,
 329 heavier aggregates used” (Mason, 2018). Dense, lightweight and AAC blocks were
 330 assumed to be 7 %, 9.5 % and 12 % cement by mass respectively. Subsequently,
 331 the cement demand from each type of concrete block can be found:

$$\text{Cement in blocks} = \frac{\text{Area of block produced}}{\text{Average area of block}} \times \text{Average mass of block} \quad (5)$$

$$\times \text{Average cement content of block (by mass)}$$

332 **Infrastructure** Cement’s infrastructural applications in the EU were broken down into
 333 transport, hydraulic works (pipes) and other infrastructure by CEMBUREAU (Rimoldi,
 334 2017). This breakdown was developed further by assuming that cement use within
 335 transport applications is directly proportional to spending in the UK construction
 336 sector (Office for National Statistics, 2015), and that we do not use cement in
 337 roads.

338 The amount of cement in *paving slabs* was found using the number of slabs
 339 installed between 2004 and 2013 (Harley and Jenkins, 2014), the average size of
 340 a slab (Kilsaran, 2016) and a cement content of 300 kg/m³ (Soutsos et al., 2011):

$$\text{Cement in paving slabs} = \frac{\text{Area of slabs (2004-2013)}}{\text{Number of years (=10)}} \times \text{Avg. thickness of slab} \quad (6)$$

$$\times \text{Avg. cement content of slab}$$

341 Cement used in *railway sleepers* was found similarly (assuming a cementitious
342 content of 12 % by mass) from the number of sleepers produced (Anonymous,
343 2011), and an estimate of the average mass of a sleeper (RailOne, 2018):

$$\begin{aligned} \text{Cement in railway sleepers} &= \text{Number of sleepers} \times \text{Avg. mass of sleeper} \\ &\times \text{Avg. cement content of sleeper} \end{aligned} \quad (7)$$

344 **Residential** The Office for National Statistics publishes house- and flat-building statis-
345 tics for England (2018a). This was scaled by population to match the UK. The
346 total amount of concrete used in residential applications is known from CEMBUREAU
347 data (CEMBUREAU, 2017); total demand for cement from houses was estimated and
348 it was assumed that the remaining material was used in flats

349 **Houses** Annual data on the roof area of new *concrete roof tiles* for houses is
350 published by the UK Government Department for Business and Strategy
351 (2017). Assuming a mass per m² of 50 kg (see *e.g.* Travis Perkins products)
352 and an average cement content in concrete of 12 % by mass, the demand for
353 cement from concrete roof tiles was calculated:

$$\begin{aligned} \text{Cement in concrete roof tiles} &= \text{Area of roof covered} \\ &\times \text{Avg. mass of tile per m}^2 \\ &\times \text{Avg. cement content of tile} \end{aligned} \quad (8)$$

354 Today, most houses employ a *concrete beam* and *dense block* construction
355 method for ground floors. It was assumed that 90 % of houses use this
356 method, and the rest use a non-cement-based solution. The average floor
357 space of a new house (assumed to be two storeys) is 88 m² (RIBA, 2011).
358 Using the average floor area and average size of a dense block, we can
359 estimate the number of dense blocks required, and the number of floor
360 beams. This is then multiplied by the number of houses and the average
361 cement content of these applications to find the amount of cement demand

362

that they account for.

$$\begin{aligned} \text{Cement in concrete floor beams} &= 90 \% \times \text{Number of floor beams per house} \\ &\quad \times \text{Number of houses} \times \text{Mass of floor beam} \\ &\quad \times \text{Avg. cement content} \end{aligned} \tag{9}$$

363

It was assumed that all new houses have double leaf walls made from concrete blocks inside and bricks outside. Blocks were assumed to be used for internal walls. This setup was modelled assuming that internal and external wall areas are equal. Using the average floor area, and assuming a cube-shaped house, the outside wall area and the number of concrete blocks required were estimated. This number aligns well with the number of AAC and lightweight blocks produced, so it was assumed for the rest of the study that all of these types of block are used in housing². Estimating the demand for concrete foundations for houses is difficult — 10 % of all concrete used in houses was assumed to be for this application.

364

365

366

367

368

369

370

371

372

373

Flats The remaining demand for residential concrete was assumed to be from flats. It was assumed that all flats are built with concrete frames, consistent with findings from interviews with structural designers. Also known are the number of flats produced (Office for National Statistics, 2018a)), while case studies provide values for the amount of concrete used per flat, of approximately 110 m³ (UK, 2017; Tarmac, 2017). This allows us to perform a check: assuming a cementitious content of concrete of around 250 kg/m³ and 41,000 flats built in the UK in 2014, this would require 1,130 kt of cementitious material. The mass of cement used in residential applications that is not used in houses is found to be 1,650 kt. The disparity in these

374

375

376

377

378

379

380

381

382

²This assumption does not affect material efficiency analysis.

383 figures may be due in part to the assumptions about concrete demand per flat
384 and (more likely) cement content of concrete. Nonetheless, they are of the
385 same order of magnitude, confirming that the approach used is acceptable.
386 The breakdown by application within flats is then calculated using the
387 method detailed in the concrete frame breakdown above.

388 **Non-residential buildings** The amount of concrete used in different types of non-
389 residential sectors — commercial, public, industrial, agriculture and ‘other non-
390 residential uses’ — in the EU was also supplied by CEMBUREAU (Rimoldi, 2017).

391 **Public buildings and commercial (offices)** The market shares of steel and con-
392 crete frames in offices and ‘other buildings’ uses the values from the Institute
393 (2016). This ‘market share’ is assumed to correspond to total m² of floor
394 area. The analysis used to find the breakdown of concrete use in concrete
395 and steel frames above found that 1.44 times more concrete is used per m²
396 of floor area in a concrete frame than a steel frame. Combining these two
397 estimates, we find that 63.6 % of the concrete used in commercial buildings
398 is in steel frames vs 36.4 % in concrete frames, while for public buildings,
399 48.3 % of the concrete used is in steel frames, with 51.7 % going to con-
400 crete frames. Within these building types, breakdowns of cement use were
401 calculated using the concrete and steel frame breakdowns described above.

402 **Industrial** According to Bishop (2001), 6 % of all concrete demand in the UK
403 was for the ground floor of industrial buildings (Bishop, 2001). All dense
404 concrete blocks not used in houses were assumed to be used for industrial
405 applications. The remaining cementitious material was categorised as ‘other
406 industrial’.

407 **Agriculture** Little information is available pertaining to agricultural uses of con-
408 crete. It is likely that there are many different applications, each demanding
409 a small share of cement, so estimating this breakdown is not critical.

410 **Repairs and maintenance** CEMBUREAU provided an estimate of how much concrete
411 is used for repairing and maintaining the existing stock of cement products
412 (CEMBUREAU, 2017). The uses of this concrete were not specified further, however
413 a breakdown of repairs in different end-sectors was found using data on spending
414 from the Office for National Statistics and estimates from Woodward and Duffy
415 (2011): 45 % in residential buildings, 45 % in non-residential buildings and 10 %
416 in infrastructure. It was assumed that houses and flats demand an equal amount of
417 cement for repairs, and that all non-residential repairs are for commercial build-
418 ings (this is an over-simplification which does not affect the results of the material
419 efficiency analysis).

420 **Precast vs ready-mix concrete frame elements** From Part I of the MFA, the total amount
421 of cement used in precast products is known. The following products were as-
422 sumed to be made from precast concrete: concrete blocks, pipes, railway sleepers,
423 roof tiles and paving slabs. It was assumed that the remainder of precast concrete
424 was used for building frame elements. As the demand for cement from the above
425 applications is known, we can estimate how much cement is used in precast
426 building frame elements (vs in-situ).

427 Non-concrete applications of cement are: mortar used to bind bricks and blocks;
428 screed used to cover floors and; renders and finishes used to cover wall surfaces. These
429 applications were assumed to have a cement content of 450 kg/m^3 (Limbachiya and
430 Kew 2008).

431 **Mortar** Demand for mortar can be calculated by assuming that it is used solely to
432 bind bricks and concrete blocks, for which production statistics are published UK
433 Government Department for Business and Strategy. Assuming that a mortar joint
434 is 10 mm and that the average dimensions of blocks and bricks are $215 \times 440 \times$
435 105 mm and $215 \times 102.5 \times 65 \text{ mm}$ respectively, the demand for mortar can be
436 calculated. An additional 10 % for waste and poor work was included. Demand

437 for mortar from each end-sector was found based on where concrete blocks and
438 bricks are used.

$$\begin{aligned} \text{Cement in mortars} &= \text{Number of blocks/bricks} \\ &\times \text{Avg. amount of mortar per block/brick} \quad (10) \\ &\times \text{Avg. cement content of mortar} \end{aligned}$$

439 **Screed** The demand for screeds was estimated assuming it is only used on concrete
440 flooring. Using the average thickness of ground floors and floor slabs from above,
441 and the total mass of cement used for these applications (which has been calculated
442 previously), the total concrete floor area can be estimated. The thickness of a
443 screed varies widely depending on its specific application (some can be structural
444 while others are just used for a smooth finish). An average thickness of 40 mm
445 was used. This calculation is sensitive to both the assumed thickness of floor
446 slabs and the thickness of screed, and is therefore at best a rough approximation.
447 As with mortars, the demand for screed from building types was broken down
448 assuming it is proportional to the demand for cement in floors.

449 **Render/finishes** Demand for cement in renders and finishes was assumed to be the
450 remainder of non-concrete demand for cementitious material. This was assumed
451 to be proportional to cement demand in offices, public buildings and flats.

452 2.2. *Material efficiency*

453 Five technical options for reducing the demand for cement were investigated: 1) post-
454 tensioning floor slabs, 2) using more precast frame elements in place of in-situ concrete,
455 3) reducing the cement content of concrete, 4) using calcined clay and limestone as a
456 cement substitute, and 5) reducing construction waste. These options provide a good
457 coverage of what is possible without changing design practices, which we consider
458 below. This analysis was verified where possible by academics and industry members.
459 Its results were combined with the results of the MFA to produce an estimate of the total

460 reduction possible. The carbon reduction enabled by each material efficiency technique
461 was also estimated. Unless otherwise stated, it was assumed that emissions savings are
462 directly proportional to cement savings.

463 The Mineral Products Association (MPA) estimate that a tonne of the UK's average
464 cementitious material is responsible for 787 kgCO₂ (Leese and Casey, 2015). Using this
465 statistic, in total UK cementitious material was responsible for approximately 10 MtCO₂
466 in 2014. The UK government reported that the cement industry was responsible for just
467 4.5 MtCO₂ (UK Government - Department for Business, Energy and Industrial Strategy,
468 2016). This implies that considerably different methods were used to calculate average
469 embodied emissions of cement. Part of this disparity is likely to be the in/exclusion of
470 imported material. To ensure that this discrepancy does not impact the results of this
471 study, percentage changes were calculated and the MPA average embodied emissions
472 value was used.

473 **Substitution with calcined clay and limestone** Up to 45 % of the clinker in cement
474 can be replaced by a coupled substitution of kaolinite-rich calcined clay (30 %) and
475 limestone (15 %) (Scrivener, 2014; Zhou et al., 2017), producing concretes that
476 are at least as strong as mixes using pure CEM I (Antoni et al., 2012; Cancio Díaz
477 et al., 2017). Replacement by a further 15 % (to 60 % in total) will produce
478 concrete that is 93 % as strong as Portland cement (Antoni et al., 2012). Global
479 penetration could replace cement by 10-20 % (Scrivener, 2018). In this work, we
480 assumed that the cement in all concrete applications could be substituted with
481 London clay (Zhou et al., 2017) and limestone by 45 %. Approximately half
482 of all mortars are used for bricks, and are therefore unlikely to bear high loads
483 meaning these mortars can be replaced by 60 % with calcined clay and limestone.
484 The remaining clinker in mortars can then be replaced by 45 %. Finishings and
485 renders do not require structural strength and can be replaced by 60 % with clay
486 and limestone. Expert estimation suggests that at least a third of all screeds are

487 structural. A value of 40 % was assigned for this proportion. This cement can
488 be replaced by up to 45 % without risking harming its properties. Clinker in
489 the remaining 60 % of screeds can be substituted 60 %. The key limiting factor
490 is local availability of raw material: in the UK, supplies are available (British
491 Geological Survey, 2009; Zhou et al., 2017). Calcined London clay embodies
492 only 70 kgCO₂/tonne (Zhou et al., 2017), while limestone has an emissions
493 intensity of 30-90 kgCO₂/tonne (a value of 60 kgCO₂/tonne was used) (Leese and
494 Casey, 2015; Hammond and Jones, 2008).

495 **Reducing the binder intensity in concrete** Designing mixes for a target strength can
496 be achieved for a wide range of cement content. For example, Obla et
497 al. (2017) observe little consistency in the relationship between cementitious
498 content (in the range 350 kg/m³ — 415 kg/m³) and compressive strength, and
499 the results suggest that cementitious content could be reduced by 30 % without
500 significant loss of strength (Obla et al., 2017). It is likely possible to allow lower
501 binder intensity than the current code prescription: Wassermann et al. (2009)
502 find that concrete 28-day strength does not vary with cement content (between
503 160-200 kg/m³), implying that 200 kg/m³ cement concretes could reduce their
504 binder contents by 20 % without loss of strength properties (Wassermann et al.,
505 2009). This study also found that various other durability indicators are unaffected.
506 For the purposes of this analysis, a 15 % possible reduction in cement content
507 was used, for all applications in concrete, as well as structural screeds.

508 **Precast concrete frames** Precast elements are made in a more controlled environment
509 with greater precision than in-situ concrete, so designers can have greater con-
510 fidence in thinner parts that use material more efficiently. More complex parts
511 such as ‘voided’ slabs that are significantly lighter and use less material can also
512 be produced. Data on the possible savings are sparse, however. The Bison Hol-
513 lowcore solution is claimed to save up to 23 % of material (Bison Precast Ltd.,

514 2007). A conservative estimate of 15 % concrete savings, that could be applied
515 to floors, beams and columns, was assumed. This saving can only be applied to
516 non-precast structural elements, which constitute 67 % of current frame elements
517 as found above. Emissions factors of precast and in-situ concretes are not reliable.
518 Bison claim that emissions savings are the same as material savings, implying
519 the cement content in their concrete is the same as the average in-situ mix (Bison
520 Precast Ltd. (2007)). Hammond and Jones (2008) estimate that precast concrete
521 is 37 % more emitting than in-situ, while a case study performed by Mao et al.
522 (2013) found precast concrete to result in 10 % less carbon emissions in two
523 residential case-studies. Certainly, the carbon embodied by precast elements
524 depends on many variables: the distance from factory to site and the cementitious
525 material content, for example. In this investigation, it was assumed that precast
526 and ready-mix concretes embody the same level of carbon. In the UK, less FA and
527 GGBFS are added to precast concrete than in-situ concrete because of their effect
528 on its setting time. A compromise between speed of production and embodied
529 carbon must be found in order to improve sustainability — this investigation
530 assumes that this is possible.

531 **Post-tensioning concrete floor slabs** This is the stressing of the steel reinforcement
532 (rebar) in concrete floor slabs, before external loads are applied, to increase the
533 proportion of concrete that is in compression. This allows thinner parts that use
534 less concrete and steel. A case study by vsl found that post-tensioning saves
535 23 % on concrete and 48 % on steel, resulting in a lowering of emissions by
536 37 % (Post Tensioning Association). A study by Miller et al. (2013) found that
537 concrete demand was reduced by 36.9 % and steel demand by 43.4 %. There
538 are also beneficial knock-on effects of post-tensioning floors slabs. Because they
539 are thinner and lighter, other structural elements can also be smaller and use
540 less cement. López-Mesa et al. (2009) find that foundations can be reduced by

541 14.3 %, columns by 25.0 % and beams by 37.6 % (López-Mesa et al., 2009). Post-
542 tensioning cannot be applied to all flooring systems; it is economical for spans
543 above roughly 6 m (Post Tensioning Association; Mineral Products Association,
544 2015b). Residential spans (in flats) generally are shorter, so it was assumed that
545 post-tensioning would not be used in residential applications. Outside of these
546 applications, post-tensioning is not commonly used (as confirmed by multiple
547 interviewees); it was assumed that a 20 % saving could be applied to 95 % of
548 (non-residential) floor slabs.

549 **Reducing construction waste** The UK construction industry contributes nearly half of
550 all landfill waste (Ajayi et al., 2016); the most efficient countries waste about
551 3 % of all concrete produced (Kazaz et al., 2015). It was assumed that there is
552 negligible waste in precast plants, so savings here can only be applied to ready-mix
553 concrete.

554 **Reducing over-design in construction** There are many ways this over-specification of
555 concrete parts is brought about: the desire to use the same formwork, unnecessary
556 corrosion protection for indoor parts, using a concrete mix that is stronger than it
557 needs to be, or using repeated elements to reduce labour costs, for instance. The
558 extent to which each results in excessive demand for cement will vary between
559 designers, buildings and parts. Unlike for steel, no data on the material over-
560 specification of cement's products can be found in the literature. Therefore, we
561 used the same headline overspecification as for steel, as it was shown to be driven
562 by the engineer's decision to favour utilisation ratios for members of 80 % of
563 the code allowance (Moynihan and Allwood, 2014; Dunant et al., 2017). In
564 interviews, we found that concrete designers are similarly cautious, leading likely
565 to a similar material under-utilisation. We have therefore assumed that the cement
566 use in structural elements could be reduced by 20 % by changing the way elements
567 are specified.

568 There are many more ways of improving the efficiency with which we use cement.
569 Using bespoke parts, perhaps with variable depth, or at the least using a wider variation
570 of elements whose material demands more closely reflect the strength needed, would be
571 considered material efficiency techniques. These could be considered in future works,
572 but are likely to only represent marginal savings.

573 2.3. Combining the map of cement flow and material efficiency improvements

574 The map of cementitious material flow, and information regarding material efficiency
575 techniques — which applications they can be applied to, how much material they save
576 and what the associated emissions reductions would be per unit of cement reduction —
577 can be combined to estimate total demand and emissions reductions.

578 There are caveats to this analysis; applying three material efficiency measures that
579 independently reduce cement demand from an application by 30 % would not result in a
580 90 % reduction. The reduction is cumulative according to Equation 11 where $R_{i,a}$ is the
581 % saving of demand for application a due to efficiency measure i .

$$\text{Total reduction for application } a \text{ (\%)} = 100 - \prod_{i=1}^n 100 - R_{i,a} \quad (11)$$

582 In this analysis, the order in which material efficiency measures are implemented affects
583 the total reduction that can be attributed to each measure (it doesn't affect the combined
584 reduction from all measures, however). This order was chosen by prioritising by the
585 state-of-readiness of each measure. Post-tensioned slabs and precast frame elements are
586 already in use. Increasing the production of precast elements would require the output
587 of the industry to roughly triple, which is more challenging than using a different design
588 and construction method for floor slabs only through post-tensioning. Post-tensioning
589 was therefore 'implemented' first. Reducing the cement content of concrete and using
590 calcined clay and limestone as cementitious substitutes were considered the next closest
591 to being implementable. Codes and standards do not exist for either technology, and
592 research into their efficacy and applicability is not complete; they were considered fairly

593 even in this sense. Reducing the cement content of concrete is more beneficial in terms
594 of emissions savings (per unit of cement demand reduction), and it is therefore logical
595 to prioritise this action over using replacement materials.

596 *2.4. Interviews with industry*

597 To verify the methods used and results obtained in this research, structural designers
598 from three leading firms (Ramboll UK Ltd., Expedition Engineering, and Price & Myers)
599 were interviewed. The interviews lasted 30-40 minute and interviewees were asked
600 direct questions about:

- 601 • the method used here for calculating the breakdown of cement demand in steel-
602 and concrete-framed buildings (all interviewees were structural designers of build-
603 ings so their areas of expertise did not encompass other topics like infrastructural
604 uses of cement),
- 605 • material efficiency techniques that could be applied to ground floors, and their
606 feasibility,
- 607 • material efficiency techniques that could be applied to floor slabs, and their feasi-
608 bility,
- 609 • the possibility of using more FA and GGBFS in concrete,
- 610 • precast vs ready-mix concrete — materials and emissions savings and why de-
611 signers/contractors choose one or the other currently, and
- 612 • repairs and maintenance — what is being repaired and how could this demand be
613 reduced.

614 Interviewees were then asked about their own general ideas pertaining to cement and
615 concrete use in the construction industry: what contributes to inefficiency and what
616 the limitations of trying to change design techniques might be, for example. All the
617 material reduction techniques proposed in this paper have been discussed and validated
618 as possible by all the interviewees.

619 3. Results

620 The results of the MFA and the investigation into material efficiency in the cement
621 industry are presented here.

622 3.1. MFA

623 Figure 3 (top) shows the UK use 10,540 kt of raw material to make 7,419 kt of clinker.
624 Approximately 2,600 kt of low-carbon FA and GGBFS and 1000 kt of other low-carbon
625 cementitious materials (accounting for 20 % of total cementitious material) and 1,935 kt
626 of imports are added to make up the 13,030 kt of cement used in the UK. Figure 3
627 (bottom) shows a breakdown of cement into its end-use applications. It shows that 83 %
628 of all cement is used in buildings, 13 % in infrastructure and 4 % for other miscellaneous
629 uses. 80 % cement ends up in concrete, 15 % in mortars and the remainder as other
630 miscellaneous forms like as a powder for soil stabilisation.

631 The demand for cement from more generalised application types is shown in Figure 4.
632 Building frame elements, at 2,922 kt, account for 22 % of all cement demand. Repairs
633 and maintenance account for 1,820 kt (14 %). Industrial and transport applications and
634 concrete blocks each consume approximately 1,000 kt (7.5 %) of cement, and building
635 foundations contribute a further 5 %. Of the non-concrete applications, screeds consume
636 the most cement, followed by renders then mortars.

637 Uncertainties for Part I of the MFA are shown in Figure 5. These values are generally
638 less than 20 %. The uncertainty in the mass of GGBFS, quicklime and limestone fines
639 being added to precast concrete is 30 %, while the amount of GGBFS being added to
640 ready-mix concrete is more uncertain, at 50 %.

641 3.2. Material efficiency

642 Total cement demand in the UK can be reduced by up to 56 %. Total carbon emissions
643 from cement demand in the UK could be reduced by 44 %, as shown by Figure 6 when
644 applying the material efficiency techniques. Figure 7 illustrates how much the demand
645 from each of cement's applications can be reduced, ranked by application. Floor slabs

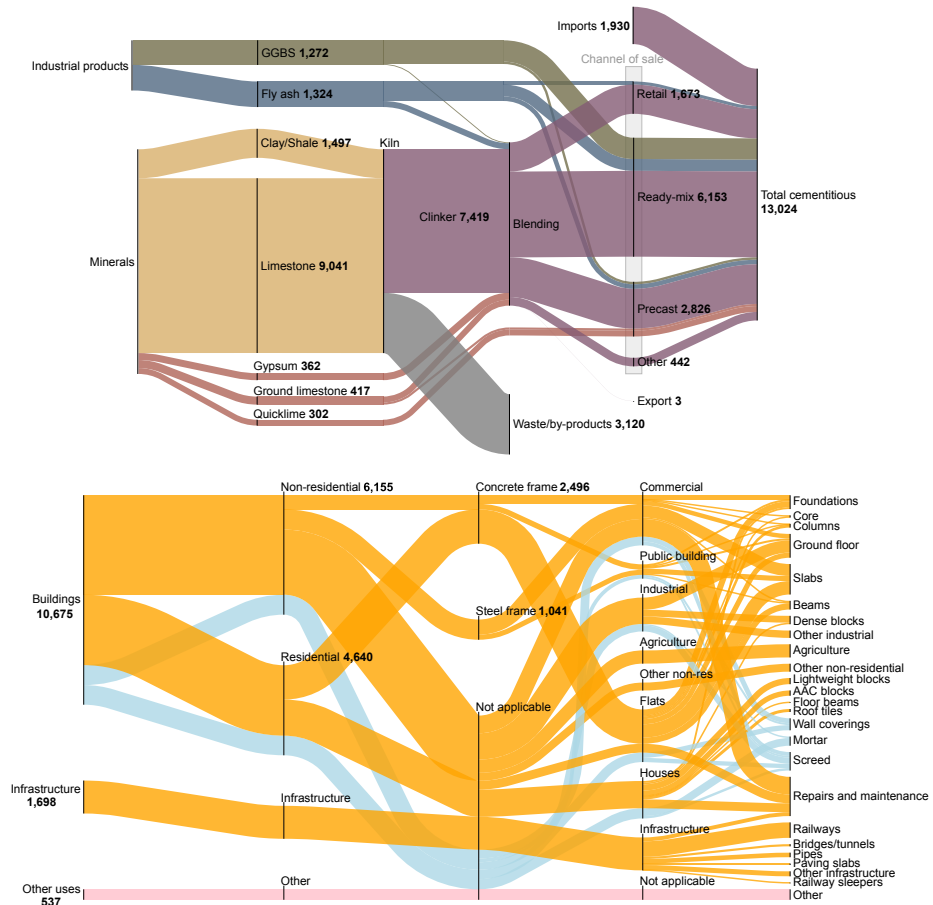


Figure 3: Numbers on the figure represent mass flow in kt. The width of the links represents mass flow while colours represent materials. **(top)** The vertical ‘slices’ represent salient processes in the production of cement. Imports mean the total amount of cementitious material in the UK’s cement industry is 13,030 kt. The sale-types of the imported cement were not determined in the MFA. **(bottom)** Slices represent applications of cement. Orange marks concrete, light blue mortars and pink powders used as soil stabilisation and other miscellaneous applications. The vertical slices represent: the industry (buildings, infrastructure, other), the construction sector (non-residential etc.), the type of structural frame (if applicable), the construction type (commercial buildings, public buildings etc.), and the final slice shows the applications themselves. Diagram produced using floWeaver (Lupton and Allwood, 2017; Lupton, 2018–)

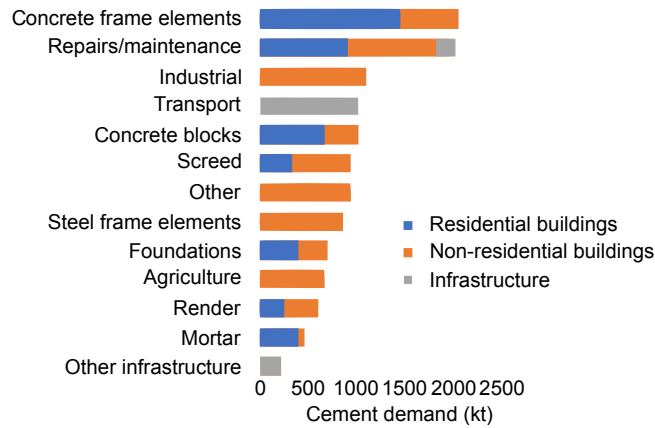


Figure 4: Cement demand by application type in the UK.

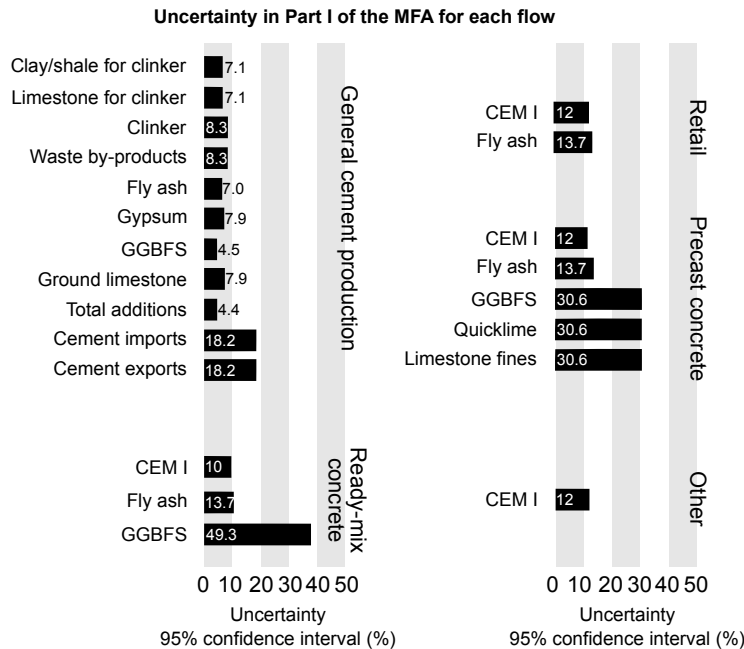


Figure 5: The results of the uncertainty analysis for Part I of the MFA. The true mass flow is expected to fall within twice the uncertainty shown of the mean.

646 and ground floors should be prioritised as they account for the highest shares of demand.
 647 Repairs and maintenance, because of their large contribution to overall demand, can be
 648 reduced by the second most in absolute terms. To achieve the reduction, a number of
 649 means are available. Using calcined clay and limestone has large potential to reduce

650 cement demand: 13 %-40 % reductions are possible, depending on clay quality is used
 651 as a substitute for cement. Reducing the binder content in concrete can reduce demand
 652 further by 10 %.

653 To produce the figures, we have multiplied the flow corresponding to the end appli-
 654 cation by the applicable efficiencies. As the result depend on the order of application, we
 655 have applied the material efficiency techniques in decreasing order of potential reduction,
 656 with the exception of optimising construction ('Reducing over-design in construction')
 657 which was applied last, as it would require a cultural change. Figure 7 and Figure 6 thus
 658 display the same data, agglomerated differently.

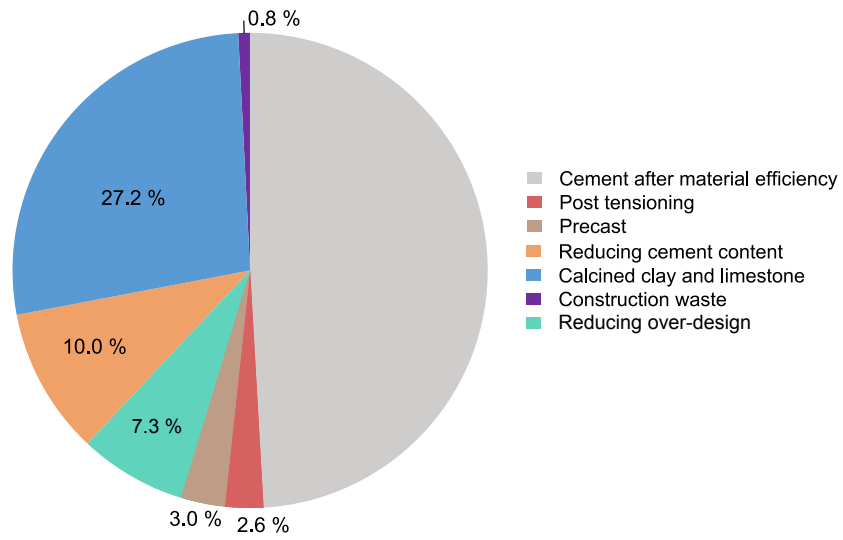


Figure 6: Pie charts showing the carbon emissions due to UK demand for cement in 2014, broken down into that which is necessary and that which could be reduced by each of six material efficiency techniques, as well as reducing over-design in construction.

659 All the methods presented above are independent of the design practice of the
 660 construction industry. We have thus decided to apply the final material efficiency
 661 technique, reducing overdesign, last. The savings from optimised design can then
 662 be found by assuming a 20 % saving to be applicable across the board in concrete
 663 structural elements in buildings: floor slabs, ground floors, foundations, beams, screeds,

664 columns and floor beams. This brings the headline figure of potential carbon abatement
665 to 51.3 %.

666 **4. Discussion**

667 *4.1. Reliability of the analysis*

668 The uncertainty analysis performed in Part I of the MFA suggests that mass flow values
669 for material inputs and cement's 'channel of sale' are reliable. Although quantitative
670 analysis of uncertainty in Part II was not performed, qualitative comments can be
671 made. The starting-point of all calculations was the CEMBUREAU statistics for end-sector
672 uses of concrete for the UK from 2007-2009 (CEMBUREAU, 2017), which were checked
673 against industry spending breakdowns (Office for National Statistics, 2015). Their close
674 agreement affirms that these data are a sound basis from which to continue estimation.
675 The uncertainty associated with the subsequent estimates for demand from individual
676 products will vary widely; some applications were calculated from direct data and so
677 can be stated with a reasonable degree of confidence. Other applications were calculated
678 through more convoluted methods, using several assumptions and case studies that
679 may not be applicable (see steel- and concrete-framed elements and foundations, for
680 example).

681 Two important simplifications may affect the results: that all products use cement
682 with the same composition (which was assessed as reasonable in interviews), and that
683 all concretes have the same cement content (which is known to be true *on average*).
684 Furthermore, simplifications were made when estimating how much a material efficiency
685 technique could reduce cement demand from an application. Post-tensioned slabs and
686 precast concrete elements were assumed to have the same emissions factors as the UK
687 average cement, which may not be the case. The results here are also dependent on the
688 order of 'implementation' of the material efficiency techniques, although sensitivity is
689 not particularly high. A summary of the uncertainty of the various techniques can be
690 found in Table 2.

Reduction in cement demand due to each material efficiency technique, for each application in the UK

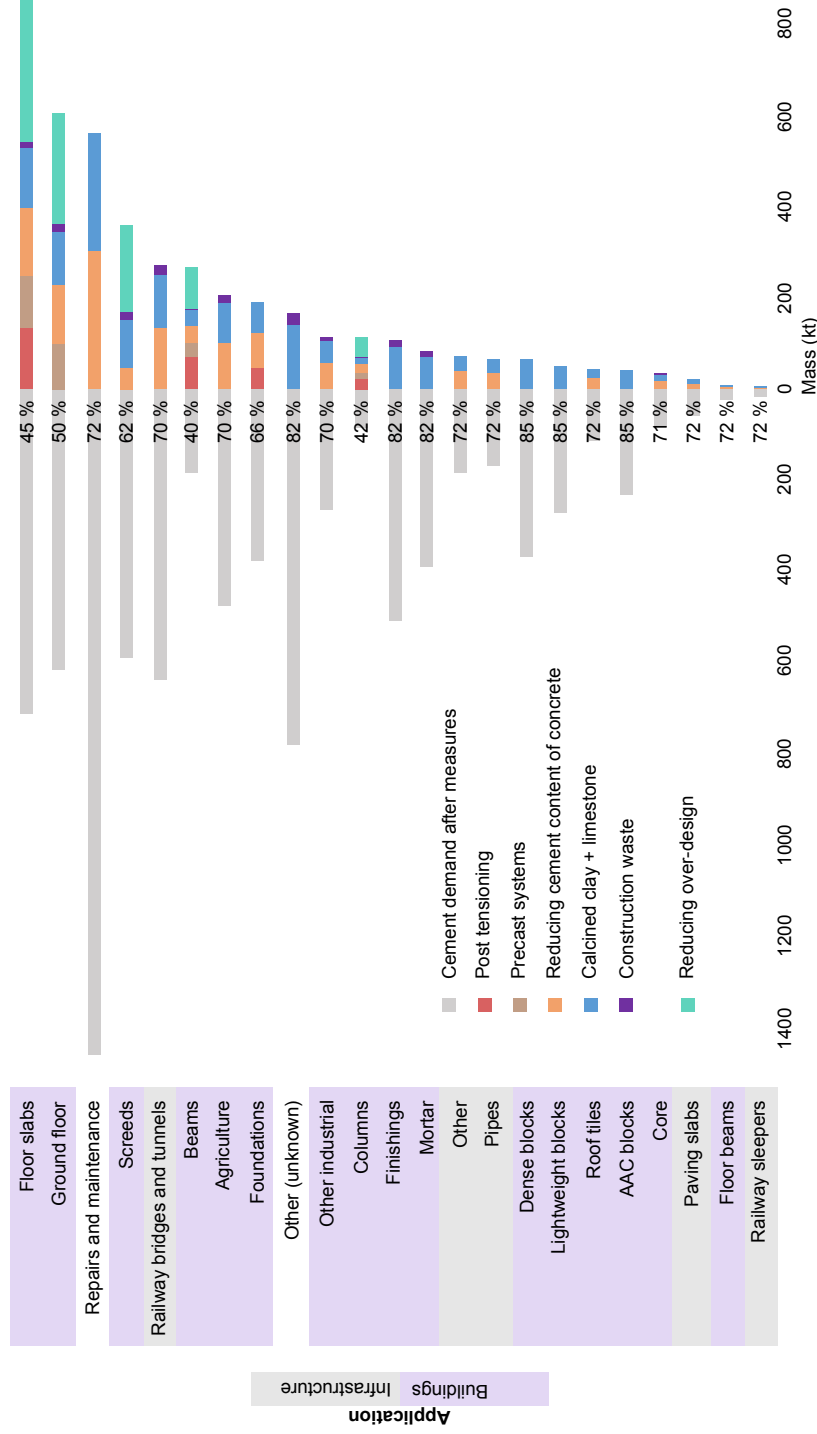


Figure 7: The application-wise results of the material efficiency analysis, ranked by the absolute demand reduction possible. The grey bars and percentages on the left show absolute and proportional cement demand remaining after all six material efficiency techniques have been applied. The coloured bars on the right represent demand reduction due to each of these techniques. The total length of the bars represents the current demand for cement for cement from each application. Therefore, the right-hand side of the graph represents a possible more efficient cement use, and on the right, the application ranked by their potential for abatement.

Table 2: Range of efficiency associated with the various techniques due to uncertainties.

| Technique | Applicability | Benefit | Total |
|--------------------|---------------|---------|----------|
| Post-tensioning | 95–100% | 14–36% | 13.3–36% |
| Precast Elements | 0–67% | 15–23% | 0–15.4% |
| Cement Content | 50–90% | 0–30% | 0–27% |
| Calcined Clay | 80–100% | 51–52% | 40.8–52% |
| Construction waste | 44–50% | 0–3% | 0–1.5% |

691 The material flow analysis was performed on a single year without consideration of
692 the possible changes to overall demand or demand from individual applications over
693 time. Demand in the UK is unlikely to change significantly compared to countries which
694 use more cement or to developing countries whose demand will increase in the coming
695 years. The results of this work suggest that material efficiency techniques related to
696 composition can have more of an impact than those related to the design of products.
697 However this is because several design techniques were not considered, such as reducing
698 the over-specification of concrete or designing for re-use. These were not included
699 because material savings were difficult to quantify, but this doesn't mean that they cannot
700 be important. The map of cement flow produced in the MFA provides data with which
701 the potential of these measures can be assessed.

702 4.2. Recommendations

703 Buildings account for a dominant share of the demand for cement. A technique
704 to improve the efficiency of a concrete application would need to target only a few
705 institutions (designers, contractors etc.) To encourage more efficient use of cement in
706 mortars would require changing the practices of many small builders, with wider set
707 of applications, which would be more difficult. Repairs and maintenance, mostly of
708 buildings, account for the largest demand of any single 'application'. More detailed
709 knowledge of what these repairs are needed for is essential to reduce this demand.
710 Nonetheless, why is there such a large need for repairs — is it poor initial design,
711 retro-fitting, or just unavoidable degradation? would attempting to reduce this demand

712 through more durable products just increase the cement needed initially, resulting in an
713 increase?

714 Demand for cement in undetermined industrial and agricultural applications is high.
715 It is likely that agricultural applications involve in-situ concrete for flooring of farms.
716 Material efficiency options are therefore limited to changing the composition of cement
717 and concrete. Design efficiency options may have more of an effect on industrial
718 applications, like concrete warehouse frames. Concrete blocks are ubiquitous, and
719 perhaps difficult to target for efficiency improvements because there are many small
720 manufacturers, requiring legislating their composition. Other significant sources of
721 cement demand include screeds, foundations, and 'other' uses. As with other mortars,
722 screeds are difficult to improve, other than through composition change. Foundations
723 have not been assessed for specific material efficiency improvements in this work.

724 Of the material efficiency options studied, changing cement and concrete's composi-
725 tions may have greater potential to reduce carbon emissions than any single design or
726 structural option. Substituting clinker in cement with calcined clay and limestone can
727 reduce UK cement demand by between 13-40 % depending on the clay used, with resul-
728 tant emissions reductions of 10-27 %. Technological research into the use of calcined
729 clay for concrete is fairly mature. In addition to reducing concrete's carbon emissions,
730 this technology can reduce costs, be produced in existing cement plants, and would
731 not require major changes to concrete technology, and has no durability downsides
732 (Scrivener, 2014). If these binders become widely available, uptake will depend largely,
733 as with the use of current additions FA and GGBFS, on early-age strength development,
734 as well as managing the workability of the new binders (Antoni et al., 2012). Nonethe-
735 less, changes to the current concrete standards are still needed for calcined clay and
736 limestone to become a viable material efficiency technique. Further, the availability
737 of these materials is the primary limiting factor for uptake in the UK in the long term,
738 and accurate determination of the emissions reductions possible through this strategy is

739 critical to its prioritisation as an efficiency technique.

740 Reducing the binder content of concrete has the potential to reduce demand and
741 carbon emissions by 10 %. As with calcined clay and limestone replacement, there
742 will need to be a change of concrete standards once the technology is proven. Concrete
743 technologists and specifiers of concrete mixes will need to be educated on this strategy
744 and encouraged to use it for all applications; this will be difficult because human
745 tendency is to overspecify requirements and ‘stay with what they know’ (as repeated
746 by interviewees). Cement manufacturers would likely resist this step because it could
747 threaten revenues.

748 Optimising construction designs would need a cultural change in the way buildings
749 are engineered. Nonetheless, this can represent a 7 % saving in emissions, if all other
750 measures are applied. Done on its own, it would represent a 20 % savings. Specific
751 technologies have less potential. Using only precast elements could reduce carbon
752 emissions by 3 %. This strategy would require a shift in the entire construction industry,
753 as well as a tripling in the capacity of precast manufacturers. Acknowledged in the
754 methodology section, and confirmed by an interviewee, the actual cement savings from
755 precast concrete are very hard to predict because there are many variables involved.
756 According to several of the interviewees, the choice of precast vs poured in-situ concrete
757 is mostly determined by logistical variables: costs, site access and crane time, for
758 example. Precast is generally used when it is cheaper, determined by the above reasons.
759 Given that possible benefits are estimated to be low and highly uncertain, pursuing this
760 option should not be of the highest priority in the UK.

761 Post-tensioning (but equally other floor slab material efficiency techniques for which
762 it acts as a surrogate) would only contribute a 2.6 % reduction in cement demand and
763 emissions. This reduction in emissions is not guaranteed, because as stated by one
764 interviewee, some post-tensioning systems use higher cement contents; in construction,
765 post-tensioning is done to save on thickness of parts and not for environmental reasons.

766 Another interviewee disagreed with this, however, arguing that the major design concerns
767 associated with post-tensioning are unrelated to cement content and so there is no reason
768 for them to use above average. It is certainly feasible to increase the use of post-
769 tensioning in building design above today's level. However, a 100 % increase is not
770 feasible, and so post-tensioning should not be pursued as a critical material efficiency
771 technique.

772 **5. Conclusions**

773 An unprecedented map of the flow of cementitious material has been developed
774 for the UK in 2014, using published data on building materials and various methods of
775 estimation. 83 % of cement is used in buildings, with the remainder (13 %) mostly
776 being used for infrastructure. Building frame elements account for the highest share
777 of demand, followed by repairs and maintenance, industrial and agricultural uses, and
778 concrete blocks. The first half of this map, Part I of a material flow analysis, carries a
779 relatively small degree of uncertainty. Using a method developed by Laner et al. (2015),
780 the uncertainties in material use and cement demand were generally estimated to be
781 $\pm 5-30$ %. Part II of this material flow analysis evaluated the demand for cement from
782 25 different applications.

783 The results of this analysis show that in terms of material demand reduction, substi-
784 tuting cement with calcined clay and limestone has by far the greatest potential, followed
785 by reducing the cement content of concrete. In total, the six technical measures inves-
786 tigated could reduce the UK's cement emissions by 44 %. Further, optimising designs
787 can bring the abatement potential to 51 %. Importantly for policy, none of these op-
788 tions would require changes in consumer habits, and only minimal changes in the way
789 buildings are designed. Rather, they need production at scale of novel but available and
790 economically viable SCM, as well as designers to have better incentives to optimise the
791 design of buildings.

792 **6. Acknowledgements**

793 We would like to warmly thank the engineers who answered our questions for their
794 invaluable help in this analysis and their expertise.

795 This work was supported by EPSRC Material demand reduction: NMZL/112, RG82144,
796 EPSRC reference: EP/N02351X/1.

797 **References**

798 Abdelrahman, A.A., 2017. Applications of sustainable post-tensioned concrete slabs.
799 Innovative Infrastructure Solutions 2, 42. URL: [https://link.springer.com/
800 article/10.1007/s41062-017-0075-6](https://link.springer.com/article/10.1007/s41062-017-0075-6), doi:10.1007/s41062-017-0075-6.

801 Ajayi, S.O., Oyedele, L.O., Akinade, O.O., Bilal, M., Owolabi, H.A., Alaka,
802 H.A., Kadiri, K.O., 2016. Reducing waste to landfill: A need for cul-
803 tural change in the UK construction industry. Journal of Building Engineer-
804 ing 5, 185–193. URL: [http://linkinghub.elsevier.com/retrieve/pii/
805 S2352710215300590](http://linkinghub.elsevier.com/retrieve/pii/S2352710215300590), doi:10.1016/j.jobe.2015.12.007.

806 Allwood, J.M., Ashby, M.F., Gutowski, T.G., Worrell, E., 2011. Material
807 efficiency: A white paper. Resources, Conservation and Recycling 55,
808 362–381. URL: [http://www.sciencedirect.com/science/article/pii/
809 S0921344910002405](http://www.sciencedirect.com/science/article/pii/S0921344910002405), doi:10.1016/j.resconrec.2010.11.002.

810 Anonymous, 2011. Mandate AO/008: Network Rail Materials Costs Benchmark-
811 ing Study. Technical Report. Network Rail and the Office of Rail Regula-
812 tion. URL: [http://orr.gov.uk/_data/assets/pdf_file/0003/10011/
813 benchmarking_2011_arup_report.pdf](http://orr.gov.uk/_data/assets/pdf_file/0003/10011/benchmarking_2011_arup_report.pdf).

814 Antoni, M., Rossen, J., Martirena, F., Scrivener, K., 2012. Cement substitution by
815 a combination of metakaolin and limestone. Cement and Concrete Research 42,

816 1579–1589. URL: [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0008884612002074)
817 [S0008884612002074](http://www.sciencedirect.com/science/article/pii/S0008884612002074), doi:10.1016/j.cemconres.2012.09.006.

818 Bishop, J., 2001. The early age behaviour of concrete industrial ground floor slabs.
819 Ph.D. thesis. Loughborough University. URL: [https://dspace.lboro.ac.uk/](https://dspace.lboro.ac.uk/dspace-jspui/handle/2134/6786)
820 [dspace-jspui/handle/2134/6786](https://dspace.lboro.ac.uk/dspace-jspui/handle/2134/6786).

821 Bison Precast Ltd., 2007. Precast Concrete Flooring. Technical Report. URL:
822 <http://www.bison.co.uk/pdf/hcf.pdf>.

823 British Geological Survey, 2009. Kaolin. Technical Report. URL: [http://www.bgs.](http://www.bgs.ac.uk/)
824 [ac.uk/](http://www.bgs.ac.uk/).

825 British Geological Survey, 2014. Mineral Planning Factsheet - Cement.
826 Technical Report. URL: [http://www.bgs.ac.uk/mineralsUK/planning/](http://www.bgs.ac.uk/mineralsUK/planning/mineralPlanningFactsheets.html)
827 [mineralPlanningFactsheets.html](http://www.bgs.ac.uk/mineralsUK/planning/mineralPlanningFactsheets.html).

828 British Precast - Mineral Products Association, 2015. Sustainability Mat-
829 ters 2015. Technical Report. Mineral Products Association. URL:
830 [https://www.britishprecast.org/Precast/media/BPMediaLibrary/](https://www.britishprecast.org/Precast/media/BPMediaLibrary/Publications/Pubs)
831 [Publications/Pubs](https://www.britishprecast.org/Precast/media/BPMediaLibrary/Publications/Pubs).

832 Broadhead, E., 2017. Mapping the Resource Flow of Cement. Fourth Year Project.
833 CUED.

834 Brunner, P.H., Rechberger, H., 2003. Practical Handbook of Material Flow Analysis. 1
835 edition ed., CRC Press, Boca Raton, FL.

836 Building and Construction Authority, 2012. Sustainable Construction - A Guide
837 on Concrete Usage Index. Technical Report. Building and Construction Author-
838 ity. Singapore. URL: [https://www.bca.gov.sg/SustainableConstruction/](https://www.bca.gov.sg/SustainableConstruction/others/sc_cui_final.pdf)
839 [others/sc_cui_final.pdf](https://www.bca.gov.sg/SustainableConstruction/others/sc_cui_final.pdf).

840 UK Government Department for Business, E., Strategy, I., 2017. Monthly Statistics
841 of Building Materials and Components - June 2017. Technical Report. UK Govern-
842 ment. URL: [https://www.gov.uk/government/uploads/system/uploads/](https://www.gov.uk/government/uploads/system/uploads/attachment_data/file/624737/17-cs7_-_Construction_Building_)
843 [attachment_data/file/624737/17-cs7_-_](https://www.gov.uk/government/uploads/system/uploads/attachment_data/file/624737/17-cs7_-_Construction_Building_)
844 [Construction_Building_](https://www.gov.uk/government/uploads/system/uploads/attachment_data/file/624737/17-cs7_-_Construction_Building_)
[Materials_-_Bulletin_June_2017.pdf](https://www.gov.uk/government/uploads/system/uploads/attachment_data/file/624737/17-cs7_-_Construction_Building_).

845 Cancio Díaz, Y., Sánchez Berriel, S., Heierli, U., Favier, A.R., Sánchez Machado,
846 I.R., Scrivener, K.L., Martirena Hernández, J.F., Habert, G., 2017. Lime-
847 stone calcined clay cement as a low-carbon solution to meet expanding ce-
848 ment demand in emerging economies. *Development Engineering* 2, 82–
849 91. URL: [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S2352728516300240)
850 [S2352728516300240](http://www.sciencedirect.com/science/article/pii/S2352728516300240), doi:10.1016/j.deveng.2017.06.001.

851 Cao, Z., Shen, L., Liu, L., Zhao, J., Zhong, S., Kong, H., Sun, Y., 2017a. Estimating the
852 in-use cement stock in China: 1920–2013. *Resources, Conservation and Recycling*
853 122, 21–31. doi:10.1016/j.resconrec.2017.01.021.

854 Cao, Z., Shen, L., Lovik, A.N., Müller, D.B., Liu, G., 2017b. Elaborating the history
855 of our cementing societies: an in-use stock perspective. *Environmental Science &*
856 *Technology* 51, 11468–11475.

857 CBA, 2008. *Aggregate Concrete Blocks - A Guide to Selection & Specification*.
858 Technical Report. Concrete Block Association. URL: [http://www.thakeham.co.](http://www.thakeham.co.uk/images/upload/docum/Block%20Selector.pdf)
859 [uk/images/upload/docum/Block%20Selector.pdf](http://www.thakeham.co.uk/images/upload/docum/Block%20Selector.pdf).

860 CEMBUREAU, 2017. Cement consumption, by end uses of cement. Obtained through
861 private communication.

862 Coelho, E., Candeias, P., Anamateros, G., Zaharia, R., Taucer, F., Pinto, A.V., 2004. As-
863 sessment of the seismic behaviour of RC flat slab building structures, in: *Proceedings*
864 *of 13th world conference on earthquake engineering*. Vancouver (BC): IAEE.

865 Damineli, B., John, V., 2012. Developing Low CO₂ concretes: Is clinker replacement
866 sufficient? The need of cement use efficiency improvement. *Key Engineering*
867 *Materials* 517, 342–351. doi:10.4028/www.scientific.net/KEM.517.342.

868 Department for Business, Energy & Industrial Strategy, Mineral Products Asso-
869 ciation, 2017. *Industrial Decarbonisation and Energy Efficiency Roadmap.*
870 *Technical Report.* URL: [https://www.gov.uk/government/publications/
871 industrial-decarbonisation-and-energy-efficiency-roadmaps-to-2050.](https://www.gov.uk/government/publications/industrial-decarbonisation-and-energy-efficiency-roadmaps-to-2050)

872 Dewar, J., 2003. Concrete mix design, in: *Advanced Concrete Technology*, pp. 3–40.
873 doi:10.1016/B978-075065686-3/50287-1.

874 Dunant, C., Drewniok, M., Eleftheriadis, S., Cullen, J., Allwood, J., 2017. Regularity
875 and optimisation practice in steel structural frames in real design cases. *Resources,*
876 *Conservation and Recycling* .

877 EN BS 197-1, 2000. *Cement-Part 1: Composition, specifications and conformity criteria*
878 *for common cements. Standard. British Standards Institution.*

879 European Ready Mixed Concrete Organization, 2017. *Ready-Mixed Concrete In-*
880 *dustry Statistics - Year 2015. Technical Report.* URL: [http://www.ermco.eu/
881 document/ermco-statistics-2015-final-pdf/.](http://www.ermco.eu/document/ermco-statistics-2015-final-pdf/)

882 Eyre, J.R., 2006. Membrane action in ground-bearing concrete slabs. *Proceed-*
883 *ings of the Institution of Civil Engineers - Structures and Buildings* 159, 153–
884 163. URL: [https://www.icevirtuallibrary.com/doi/abs/10.1680/stbu.
885 2006.159.3.153](https://www.icevirtuallibrary.com/doi/abs/10.1680/stbu.2006.159.3.153), doi:10.1680/stbu.2006.159.3.153.

886 Fernández, J., 2007. Resource consumption of new urban construction in China. *Journal*
887 *of Industrial Ecology* 11, 99–115. doi:10.1162/jie.2007.1199.

888 Formichi, P., 2008. *Eurocode 1 - Actions on Building Structures.* URL: [http://
889 eurocodes.jrc.ec.europa.eu/doc/Moscow08/Moscow08_9_Formichi.pdf.](http://eurocodes.jrc.ec.europa.eu/doc/Moscow08/Moscow08_9_Formichi.pdf)

890 Gao, T., Shen, L., Shen, M., Liu, L., Chen, F., 2016. Analysis of material flow and
891 consumption in cement production process. *Journal of Cleaner Production* 112,
892 553–565. URL: [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0959652615011440)
893 [S0959652615011440](http://www.sciencedirect.com/science/article/pii/S0959652615011440), doi:10.1016/j.jclepro.2015.08.054.

894 Government of the United Kingdom, 2008. Climate Change Act.

895 Griffin, P., Hammond, G., Norman, J., 2014. Prospects for emissions reduction in the UK
896 cement sector. *Proceedings of Institution of Civil Engineers: Energy* 167, 152–161.
897 doi:10.1680/ener.14.00007.

898 Hammond, G., Jones, C., 2008. Embodied energy and carbon in construction materials.
899 *Proceedings of Institution of Civil Engineers: Energy* 161, 87–98. doi:10.1680/
900 [ener.2008.161.2.87](https://doi.org/10.1680/ener.2008.161.2.87).

901 Harley, M., Jenkins, C., 2014. Research to ascertain the proportion of block paving sales
902 in England that are permeable. Technical Report. Adaptation Sub-Committee, Com-
903 mittee on Climate Change. URL: [https://www.theccc.org.uk/wp-content/](https://www.theccc.org.uk/wp-content/uploads/2014/07/7-ASC-paving-survey-report_for-publication.pdf)
904 [uploads/2014/07/7-ASC-paving-survey-report_for-publication.pdf](https://www.theccc.org.uk/wp-content/uploads/2014/07/7-ASC-paving-survey-report_for-publication.pdf).

905 Van den Heede, P., De Belie, N., 2012. Environmental impact and life
906 cycle assessment (LCA) of traditional and ‘green’ concretes: Literature re-
907 view and theoretical calculations. *Cement and Concrete Composites* 34,
908 431–442. URL: [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0958946512000054)
909 [S0958946512000054](http://www.sciencedirect.com/science/article/pii/S0958946512000054), doi:10.1016/j.cemconcomp.2012.01.004.

910 Institute, S.C., 2016. Cost of structural steelwork. URL: [https://www.](https://www.steelconstruction.info/Cost_of_structural_steelwork)
911 [steelconstruction.info/Cost_of_structural_steelwork](https://www.steelconstruction.info/Cost_of_structural_steelwork).

912 International Energy Agency, 2018. Technology Roadmap - Low-Carbon Transition
913 in the Cement Industry. Technical Report. URL: [https://webstore.iea.org/](https://webstore.iea.org/technology-roadmap-low-carbon-transition-in-the-cement-industry)
914 [technology-roadmap-low-carbon-transition-in-the-cement-industry](https://webstore.iea.org/technology-roadmap-low-carbon-transition-in-the-cement-industry).

915 International Energy Agency, The World Business Council for Sustainable
916 Development, 2009. Cement Roadmap. Technical Report. URL:
917 {[https://www.iea.org/publications/freepublications/publication/
918 Cement_Roadmap_Foldout_WEB.pdf](https://www.iea.org/publications/freepublications/publication/Cement_Roadmap_Foldout_WEB.pdf)}.

919 Kapur, A., Keoleian, G., Kendall, A., Kesler, S., 2008. Dynamic modeling of in-use
920 cement stocks in the United States. *Journal of Industrial Ecology* 12, 539–556+4.
921 doi:10.1111/j.1530-9290.2008.00055.x.

922 Kazaz, A., Ulubeyli, S., Er, B., Arslan, V., Arslan, A., Atici, M., 2015. Fresh Ready-
923 mixed Concrete Waste in Construction Projects: A Planning Approach. *Procedia
924 Engineering* 123, 268–275. URL: [http://www.sciencedirect.com/science/
925 article/pii/S1877705815031896](http://www.sciencedirect.com/science/article/pii/S1877705815031896), doi:10.1016/j.proeng.2015.10.088.

926 Kilsaran, 2016. Specification & Installation Guidance. Technical Re-
927 port. URL: [http://www.kilsaraninternational.co.uk/uploaded/
928 53199bbbe60f19.58440664.pdf](http://www.kilsaraninternational.co.uk/uploaded/53199bbbe60f19.58440664.pdf).

929 Laner, D., Feketitsch, J., Rechberger, H., Fellner, J., 2015. A Novel Approach to Char-
930 acterize Data Uncertainty in Material Flow Analysis and its Application to Plastics
931 Flows in Austria. *Journal of Industrial Ecology* 20, 1050–1063. URL: [http:
932 //onlinelibrary.wiley.com/doi/10.1111/jiec.12326/abstract](http://onlinelibrary.wiley.com/doi/10.1111/jiec.12326/abstract), doi:10.
933 1111/jiec.12326.

934 Leese, R., Casey, D., 2015. Embodied CO_{2e} of UK cement, additions and cementitious
935 material. Technical Report. Mineral Products Association. URL: [http://cement.
936 mineralproducts.org/documents/Factsheet_18.pdf](http://cement.mineralproducts.org/documents/Factsheet_18.pdf).

937 Li, J., Tharakan, P., Macdonald, D., Liang, X., 2013. Technological, economic and
938 financial prospects of carbon dioxide capture in the cement industry. *Energy Policy*
939 61, 1377–1387. URL: [http://www.sciencedirect.com/science/article/
940 pii/S0301421513004370](http://www.sciencedirect.com/science/article/pii/S0301421513004370), doi:10.1016/j.enpol.2013.05.082.

- 941 Limbachiya, M.C., Kew, H.Y., 2008. Excellence in Concrete Construction through
942 Innovation: Proceedings of the conference held at the Kingston University, United
943 Kingdom, 9 - 10 September 2008. CRC Press. Google-Books-ID: FOZTNIDN3cYC.
- 944 Low, M.S., 2005. Material flow analysis of concrete in the United States. Thesis.
945 Massachusetts Institute of Technology. URL: [http://dspace.mit.edu/handle/](http://dspace.mit.edu/handle/1721.1/33030)
946 [1721.1/33030](http://dspace.mit.edu/handle/1721.1/33030).
- 947 Lupton, R.C., 2018-. floWeaver. <https://github.com/ricklupton/floweaver>.
948 doi:<https://doi.org/10.5281/zenodo.596249>.
- 949 Lupton, R.C., Allwood, J.M., 2017. Hybrid Sankey diagrams: Visual analysis of
950 multidimensional data for understanding resource use. Resources, Conservatin &
951 Recycling 124. URL: [https://www.repository.cam.ac.uk/handle/1810/](https://www.repository.cam.ac.uk/handle/1810/265367)
952 [265367](https://www.repository.cam.ac.uk/handle/1810/265367), doi:10.17863/CAM.11266.
- 953 López-Mesa, B., Pitarch, A., Tomás, A., Gallego, T., 2009. Comparison of environmen-
954 tal impacts of building structures with in situ cast floors and with precast concrete
955 floors. Building and Environment 44, 699–712. doi:10.1016/j.buildenv.2008.
956 05.017.
- 957 Mao, C., Shen, Q., Shen, L., Tang, L., 2013. Comparative study of greenhouse gas
958 emissions between off-site prefabrication and conventional construction methods:
959 Two case studies of residential projects. Energy and Buildings 66, 165–176. doi:10.
960 1016/j.enbuild.2013.07.033.
- 961 Mason, J., 2018. Concrete block design query. Technical Report. Private communica-
962 tion.
- 963 Mathieu, P., 2006. The IPCC special report on carbon dioxide capture and storage, pp.
964 1611–1618.

- 965 McEvoy, D., Ravetz, J., Handley, J., 2004. Managing the Flow of Construc-
966 tion Minerals in the North West Region of England. *Journal of Industrial Ecol-*
967 *ogy* 8, 121–140. URL: [http://onlinelibrary.wiley.com/doi/10.1162/](http://onlinelibrary.wiley.com/doi/10.1162/1088198042442289/abstract)
968 [1088198042442289/abstract](http://onlinelibrary.wiley.com/doi/10.1162/1088198042442289), doi:10.1162/1088198042442289.
- 969 Miller, D., Doh, J., Guan, H., Mulvey, M., Fragomeni, S., McCarthy, T., Peters, T.,
970 2013. Environmental impact assessment of post tensioned and reinforced concrete
971 slab construction. *Faculty of Engineering and Information Sciences - Papers: Part*
972 *A*, 1009–1014 URL: <http://ro.uow.edu.au/eispapers/1541>, doi:10.1201/
973 b15320-180.
- 974 Mineral Products Association, 2015a. Annual Cementitious 2001-2014. Technical
975 Report. Mineral Products Association. URL: [http://cement.mineralproducts.](http://cement.mineralproducts.org/documents/annual-cementitious.pdf)
976 [org/documents/annual-cementitious.pdf](http://cement.mineralproducts.org/documents/annual-cementitious.pdf).
- 977 Mineral Products Association, 2015b. Concrete Design Guide - No. 7 Design of
978 post-tensioned slabs. Technical Report. URL: [https://www.istructe.org/](https://www.istructe.org/getattachment/121ff74a-3a1d-4bf0-a300-31c3a8505949/CDG)
979 [getattachment/121ff74a-3a1d-4bf0-a300-31c3a8505949/CDG](https://www.istructe.org/getattachment/121ff74a-3a1d-4bf0-a300-31c3a8505949/CDG).
- 980 Moynihan, M.C., Allwood, J.M., 2014. Utilization of structural steel in buildings. *Proc.*
981 *R. Soc. A* 470, 20140170. URL: [http://rspa.royalsocietypublishing.org/](http://rspa.royalsocietypublishing.org/content/470/2168/20140170)
982 [content/470/2168/20140170](http://rspa.royalsocietypublishing.org/content/470/2168/20140170), doi:10.1098/rspa.2014.0170.
- 983 Neal, F.R., 2002. Concrete industrial ground floors. Thomas Telford Publish-
984 ing. URL: [https://www.icevirtuallibrary.com/doi/book/10.1680/cigf.](https://www.icevirtuallibrary.com/doi/book/10.1680/cigf.31371)
985 [31371](https://www.icevirtuallibrary.com/doi/book/10.1680/cigf.31371), doi:10.1680/cigf.31371.
- 986 Obla, K., Hong, R., Lobo, C., Kim, H., 2017. Should minimum cementitious contents
987 for concrete be specified? *Transportation Research Record* 2629, 1–8. doi:10.3141/
988 2629-01.
- 989 Office for National Statistics, 2015. Construction Statistics Annual

990 Tables. Technical Report. URL: [https://www.ons.gov.uk/
991 businessindustryandtrade/constructionindustry/datasets/
992 constructionstatisticsannualtables](https://www.ons.gov.uk/businessindustryandtrade/constructionindustry/datasets/constructionstatisticsannualtables).

993 Office for National Statistics, 2018a. Construction output in Great Britain:
994 December 2017. Technical Report. URL: [https://www.ons.gov.
995 uk/businessindustryandtrade/constructionindustry/bulletins/
996 constructionoutputingreatbritain/december2017](https://www.ons.gov.uk/businessindustryandtrade/constructionindustry/bulletins/constructionoutputingreatbritain/december2017).

997 Office for National Statistics, 2018b. CPA 08:EU:IM:CVM:BOP:SA:
998 23.5. Cement, lime & plaster. URL: [https://www.ons.gov.uk/
999 businessindustryandtrade/internationaltrade/timeseries/p3ux/
1000 mq10](https://www.ons.gov.uk/businessindustryandtrade/internationaltrade/timeseries/p3ux/mq10).

1001 Office for National Statistics, 2018c. IOP:23.5-6:Man of cement,lime,plaster & art
1002 of concrete,cement, plaster:Weight. URL: [https://www.ons.gov.uk/economy/
1003 economicoutputandproductivity/output/timeseries/km34/diop](https://www.ons.gov.uk/economy/economicoutputandproductivity/output/timeseries/km34/diop).

1004 van Oss, H.G., 2017. Cement - Statistics and Information. URL: [https://minerals.
1005 usgs.gov/minerals/pubs/commodity/cement/mcs-2017-cemen.pdf](https://minerals.usgs.gov/minerals/pubs/commodity/cement/mcs-2017-cemen.pdf).

1006 Post Tensioning Association, . Developer. URL: [http://www.posttensioning.co.
1007 uk/developer/](http://www.posttensioning.co.uk/developer/).

1008 UK Quality Ash Association, 2016. Ash Statistics for 2014.
1009 URL: [http://www.ukqaa.org.uk/wp-content/uploads/
1010 Annual-ash-statistics-2014-Public-domain-table-bar-chart.pdf](http://www.ukqaa.org.uk/wp-content/uploads/Annual-ash-statistics-2014-Public-domain-table-bar-chart.pdf).

1011 RailOne, 2018. Concrete Sleepers. Technical Report. Rail.One.
1012 URL: [https://www.railone.com/fileadmin/daten/05-presse-medien/
1013 downloads/broschueren/en/ConcreteSleepers_2014_EN.pdf](https://www.railone.com/fileadmin/daten/05-presse-medien/downloads/broschueren/en/ConcreteSleepers_2014_EN.pdf).

- 1014 RIBA, 2011. The Case for Space. Technical Report. Royal Institute of
1015 British Architects. URL: [https://www.architecture.com/-/media/
1016 gathercontent/space-standards-for-homes/additional-documents/
1017 ribacaseforspace2011pdf.pdf](https://www.architecture.com/-/media/gathercontent/space-standards-for-homes/additional-documents/ribacaseforspace2011pdf.pdf).
- 1018 Rimoldi, A., 2017. Cement and concrete flow. Technical Report. Private communica-
1019 tion.
- 1020 Schneider, M., Romer, M., Tschudin, M., Bolio, H., 2011. Sustainable ce-
1021 ment production—present and future. Cement and Concrete Research 41,
1022 642–650. URL: [http://www.sciencedirect.com/science/article/pii/
1023 S0008884611000950](http://www.sciencedirect.com/science/article/pii/S0008884611000950), doi:10.1016/j.cemconres.2011.03.019.
- 1024 Scrivener, K., 2014. Options for the future of cement. Indian Concrete Journal 88,
1025 11–21.
- 1026 Scrivener, K.L., 2018. Potential LC3 penetration. Obtained through private communi-
1027 cation.
- 1028 Soutsos, M.N., Tang, K., Millard, S.G., 2011. Use of recycled demolition aggregate
1029 in precast products, phase II: Concrete paving blocks. Construction and Building
1030 Materials 25, 3131–3143. URL: [http://www.sciencedirect.com/science/
1031 article/pii/S0950061810007014](http://www.sciencedirect.com/science/article/pii/S0950061810007014), doi:10.1016/j.conbuildmat.2010.12.
1032 024.
- 1033 Summerbell, D., Khripko, D., Barlow, C., Hesselbach, J., 2017. Cost and carbon
1034 reductions from industrial demand-side management: Study of potential savings at a
1035 cement plant. Applied Energy 197, 100–113. doi:10.1016/j.apenergy.2017.03.
1036 083.
- 1037 Sun, J.C., Wang, B.J., Zhao, W.Z., 2013. Experimental study on the impact of admix-
1038 ture for concrete heat of hydration and early-age contractile properties. Applied

1039 Mechanics and Materials 253-255, 385-389. doi:10.4028/www.scientific.net/
1040 AMM.253-255.385.

1041 Tang, K., Millard, S., Beattie, G., 2015. Early-age heat development in GGBS concrete
1042 structures. Proceedings of the Institution of Civil Engineers - Structures and Buildings
1043 168, 541-553. URL: [https://www.icevirtuallibrary.com/doi/full/10.](https://www.icevirtuallibrary.com/doi/full/10.1680/stbu.14.00089)
1044 [1680/stbu.14.00089](https://www.icevirtuallibrary.com/doi/full/10.1680/stbu.14.00089), doi:10.1680/stbu.14.00089.

1045 Tarmac, 2017. Proven Performance - One Blackfriars, Southwark, London. Tech-
1046 nical Report. Tarmac. URL: [http://www.tarmac.com/media/959418/](http://www.tarmac.com/media/959418/topflow-one-blackfriars-case-study.pdf)
1047 [topflow-one-blackfriars-case-study.pdf](http://www.tarmac.com/media/959418/topflow-one-blackfriars-case-study.pdf).

1048 Teh, S.H., Wiedmann, T., Castel, A., de Burgh, J., 2017. Hybrid life
1049 cycle assessment of greenhouse gas emissions from cement, concrete and
1050 geopolymer concrete in Australia. Journal of Cleaner Production 152, 312-
1051 320. URL: [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0959652617305668)
1052 [S0959652617305668](http://www.sciencedirect.com/science/article/pii/S0959652617305668), doi:10.1016/j.jclepro.2017.03.122.

1053 UK, H., 2017. Lexicon, Islington, London EC1 - Project case study. Technical Report.
1054 Hanson UK. URL: <https://www.hanson.co.uk/en/case-study/lexicon>.

1055 UK Government, 2010. English Housing Survey. Technical Re-
1056 port. URL: [https://assets.publishing.service.gov.uk/government/](https://assets.publishing.service.gov.uk/government/uploads/system/uploads/attachment_data/file/6703/1750754.pdf)
1057 [uploads/system/uploads/attachment_data/file/6703/1750754.pdf](https://assets.publishing.service.gov.uk/government/uploads/system/uploads/attachment_data/file/6703/1750754.pdf).

1058 UK Government, 2016. Mineral extraction in Great Britain 2014. Technical
1059 Report. URL: [https://assets.publishing.service.gov.uk/government/](https://assets.publishing.service.gov.uk/government/uploads/system/uploads/attachment_data/file/505631/Mineral_)
1060 [uploads/system/uploads/attachment_data/file/505631/Mineral_](https://assets.publishing.service.gov.uk/government/uploads/system/uploads/attachment_data/file/505631/Mineral_)
1061 [Extraction_in_Great_Britain_2014_final.pdf](https://assets.publishing.service.gov.uk/government/uploads/system/uploads/attachment_data/file/505631/Mineral_).

1062 UK Government - Competition Commission, 2016. Aggregates, Cement and Ready-

1063 mix Concrete Market Investigation. URL: <https://www.gov.uk/cma-cases/aggregates-cement-and-ready-mix-concrete-market-investigation>.

1064

1065 UK Government - Department for Business, Energy and Industrial Strategy, 2016.

1066 Final UK greenhouse gas emissions national statistics 1990-2015. Technical Re-

1067 port. UK Government. URL: [https://www.gov.uk/government/statistics/](https://www.gov.uk/government/statistics/final-uk-greenhouse-gas-emissions-national-statistics-1990-2015)

1068 [final-uk-greenhouse-gas-emissions-national-statistics-1990-2015](https://www.gov.uk/government/statistics/final-uk-greenhouse-gas-emissions-national-statistics-1990-2015).

1069 Wang, W., Jiang, D., Chen, D., Chen, Z., Zhou, W., Zhu, B., 2016. A Material

1070 Flow Analysis (MFA)-based potential analysis of eco-efficiency indicators of China's

1071 cement and cement-based materials industry. *Journal of Cleaner Production* 112,

1072 787–796. URL: [http://www.sciencedirect.com/science/article/pii/](http://www.sciencedirect.com/science/article/pii/S0959652615008367)

1073 [S0959652615008367](http://www.sciencedirect.com/science/article/pii/S0959652615008367), doi:10.1016/j.jclepro.2015.06.103.

1074 Wassermann, R., Katz, A., Bentur, A., 2009. Minimum cement content requirements:

1075 A must or a myth? *Materials and Structures/Materiaux et Constructions* 42, 973–982.

1076 doi:10.1617/s11527-008-9436-0.

1077 Wille, K., Boisvert-Cotulio, C., 2015. Material efficiency in the design

1078 of ultra-high performance concrete. *Construction and Building Materials*

1079 86, 33–43. URL: [http://linkinghub.elsevier.com/retrieve/pii/](http://linkinghub.elsevier.com/retrieve/pii/S0950061815003451)

1080 [S0950061815003451](http://linkinghub.elsevier.com/retrieve/pii/S0950061815003451), doi:10.1016/j.conbuildmat.2015.03.087.

1081 Woodward, R., Duffy, N., 2011. Cement and concrete flow analysis in a rapidly

1082 expanding economy: Ireland as a case study. *Resources, Conservation and Recycling*

1083 55, 448–455. doi:10.1016/j.resconrec.2010.12.006.

1084 World Business Council for Sustainable Development - Cement Sustainability Initia-

1085 tive, 2016. Getting the Numbers Right. URL: [http://www.wbcscement.org/](http://www.wbcscement.org/GNR-2013/index.html)

1086 [GNR-2013/index.html](http://www.wbcscement.org/GNR-2013/index.html).

1087 Zhou, D., Wang, R., Tyrer, M., Wong, H., Cheeseman, C., 2017. Sustainable

1088 infrastructure development through use of calcined excavated waste clay as a
1089 supplementary cementitious material. Journal of Cleaner Production 168, 1180–
1090 1192. URL: [https://pureportal.coventry.ac.uk/en/publications/
1091 sustainable-infrastructure-development-through-use-of-calcined-ex,](https://pureportal.coventry.ac.uk/en/publications/sustainable-infrastructure-development-through-use-of-calcined-ex)
1092 [doi:10.1016/j.jclepro.2017.09.098](https://doi.org/10.1016/j.jclepro.2017.09.098).